



Oxidative decomposition mechanisms of lithium carbonate on carbon substrates in lithium battery chemistries

Dr. Sudhir Kumar Mishra,

Principal, S.S. College, Jehanabad,

Email: innovationskmishra@gmail.com

Abstract

Lithium carbonate plays a critical role in both lithium-carbon dioxide and lithium-air batteries as the main discharge product and a product of side reactions, respectively. Understanding the decomposition of lithium carbonate during electrochemical oxidation (during battery charging) is key for improving both chemistries, but the decomposition mechanisms and the role of the carbon substrate remain under debate. Here, we use an in-situ differential electrochemical mass spectrometry-gas chromatography coupling system to quantify the gas evolution during the electrochemical oxidation of lithium carbonate on carbon substrates. Our results show that lithium carbonate decomposes to carbon dioxide and singlet oxygen mainly via an electrochemical process instead of via a chemical process in an electrolyte of lithium bis(trifluoromethanesulfonyl)imide in tetraglyme. Singlet oxygen attacks the carbon substrate and electrolyte to form both carbon dioxide and carbon monoxide—approximately 20% of the net gas evolved originates from these side reactions. Additionally, we show that cobalt(II,III) oxide, a typical oxygen evolution catalyst, stabilizes the precursor of singlet oxygen, thus inhibiting the formation of singlet oxygen and consequent side reactions.

Keywords: *Overpotential, Gas chromatography, Singlet oxygen, DMS, ^{13}C -substrate, Superoxide, Electrooxidative process, Electrolyte degradation.*

Introduction

Lithium carbonate (Li_2CO_3) is involved in many electrochemical systems, such as lithium-oxygen (Li-O_2) batteries^{1–15}, lithium-carbon dioxide (Li-CO_2) batteries^{16–30}, and lithium-ion (Li-ion) batteries^{31–43}. Li_2CO_3 has extremely low ionic and electronic conductivity due to its wide bandgap^{44,45}. In Li-O_2 batteries, Li_2CO_3 mainly results from the side reactions of the reduced oxygen species attacking the electrolytes^{1–3}. It not only passivates the electrode surface and polarizes the cell but also consumes the electrolyte, leading to electrolyte depletion and premature cell death. Therefore, Peng et al. referred to Li_2CO_3 as the “Achilles’ Heel” because it dominates the electrochemical performance of cells³. The accumulation of Li_2CO_3 during cycling has to be well-addressed and resolved in the pursuit of high-performance Li-O_2 batteries. In Li-CO_2 batteries, Li_2CO_3 is the main desirable discharge product, but the Li_2CO_3 decomposition during charging has sluggish kinetics and requires a large overpotential. Many efforts have been devoted to designing highly efficient catalysts to reduce the large overpotential^{18–29}. In both Li-O_2 batteries and Li-CO_2 batteries, Li_2CO_3 in the composite electrode needs to be oxidatively decomposed during the charging process, otherwise, it passivates the electrode surface and kills the cells. However, the mechanism of Li_2CO_3 decomposition is still unclear and this would seriously hinder the research progress. For instance, the role of carbon in the charging process is still under debate. In Li-ion batteries, Li_2CO_3 is one of the main components of the solid electrolyte interphase of the anode and exists as a surface contaminant present on lithium transition metal oxides used in the cathode thus it influences the cell performance³². For instance, the lithium transition metal oxides cathode materials are usually covered with a layer of Li_2CO_3 due to the residual lithium precursors reacting with CO_2 from the ambient atmosphere^{33–35}. Very recently, McCloskey and coworkers have studied the Li_2CO_3 decomposition mechanism on Li-ion cathodes. Using isotopic labeling, they found that when Li_2CO_3 is present at the cathode surface, organic fragments containing diatomic oxygen are formed on the cathode surface during the charging process above 4.2 V versus Li^+/Li and the diatomic oxygen within these fragments mainly originates from the lithium transition metal oxides lattice and only a minor fraction originates from the Li_2CO_3 itself^{33–35}. In summary, the decomposition of Li_2CO_3 is so important that it determines the electrochemical performance in many systems. However, its mechanisms are still controversial and not yet well understood, even in the Li-CO_2 cells. Li_2CO_3 decomposition during the charging process is generally divided into two types, chemical routes, and electrochemical routes^{41,42}. Recently, Freiberg et al. claimed that Li_2CO_3 decomposition in lithium hexafluorophosphate (LiPF_6)-ethylene carbonate (EC)-ethylmethyl carbonate (EMC) electrolyte follows a chemical route reacting with H^+ , which is induced by electrolyte oxidation at >4.6 V⁴¹. In contrast, Mahne et al. claimed that Li_2CO_3 decomposition is an electrochemical process^{33,46}. Here, our results show that the electrolyte salt affects the route and the chemical reaction is likely caused by LiPF_6 , which will be discussed later.

So far, several electrochemical mechanisms have been proposed and four possible reaction pathways are summarized below:



In Eq. (1a and b), both CO_2 and O_2 formed and it takes 2e^- per CO_2 molecule^{16,17}. The only difference is that O_2 forms as a triplet O_2 in Eq. (1a) and as a singlet O_2 (${}^1\text{O}_2$) in Eq. (1b), respectively. ${}^1\text{O}_2$ has been detected at a charging voltage above 3.8 V in the oxidation of Li_2CO_3 , by using high-performance liquid chromatography (HPLC) and nuclear magnetic resonance spectrometry (${}^1\text{H}$ NMR) analysis⁴⁶. In Eq. (2), carbon and Li_2CO_3 were oxidized together to form CO_2 via a 4e^- process. That is a common mechanism proposed for the charging process of Li^+/CO_2 cells. In fact, Eq. (2) is unlikely to be an elemental reaction, which will be discussed in the text later. In Eq. (3), oxygen is released in the form of the superoxide radical. Qiao et al.²⁷ used in situ surface-enhanced Raman spectroscopy to observe the dimethyl sulfone during the charging process and they explained that dimethyl sulfone is attributed to the nucleophilic attack on DMSO solvent from reduced oxygen species (superoxide radicals etc.).

Despite the above progress, researchers mainly focus on Li_2CO_3 and little attention has been paid to the carbon in the charging process. Carbon is always added to the composite electrodes as the conductive additives, however, it is always neglected and its role in Li_2CO_3 decomposition has not been considered yet. Overall, the mechanism of Li_2CO_3 decomposition is still under debate and the role of carbon is mysterious.

Here, we labeled the Li_2CO_3 and carbon substrate with ${}^{13}\text{C}$ -isotope and qualitatively analyzed the gas products from the decomposition of Li_2CO_3 , carbon, and electrolyte, respectively. We quantified the gas evolution, particularly CO , during the charging process using an in situ differential electrochemical mass spectroscopy-gas chromatography (DEMS-GC) coupling system. We found that Li_2CO_3 decomposition is mainly an electrochemical process rather than a chemical process induced by electrolyte oxidation. Li_2CO_3 decomposes to CO_2 only, but no CO nor O_2 . The oxygen from Li_2CO_3 is released as highly reactive ${}^1\text{O}_2$, which further attacks the electrolyte and carbon substrate in the composite electrodes to form CO_2 and CO .

Results and discussion

To study the oxidative decomposition process of Li_2CO_3 , a cell with a Li_2CO_3 -carbon composite electrode was constructed and charged. Li_2CO_3 was electro-oxidized and the gas evolution was quantified. Because both CO and N_2 have the same mass-to-charge ratio of 28 ($m/z = 28$), the mass spectrometer typically used in a DEMS system lacks sufficient mass resolution to distinguish the contribution from CO ($m/z = 28.0104$) and N_2 ($m/z = 28.0140$). Although GC could separate the CO and N_2 , it cannot distinguish and quantify the ${}^{13}\text{CO}_2/{}^{13}\text{CO}_2$ and ${}^{12}\text{CO}/{}^{13}\text{CO}$. Therefore, an in situ DEMS-GC coupling system (Supplementary

Fig. 1) was used to quantify the evolution of ^{12}CO , $^{12}\text{CO}_2$, ^{13}CO , and $^{13}\text{CO}_2$. The details of the experiments are described in Methods. As shown in Supplementary Fig. 2, after calibration, the CO evolution signals from DEMS and GC experiments are consistent, which provides a reliable amount of CO in the following experiments.

Super P carbon (Timcal) was ball milled with Li_2CO_3 with a mass ratio of 1:1. A Li_2CO_3 - Super P (1:1) composite electrode was prepared to construct a cell with 1M lithiumbis(trifluoromethane-sulfonyl)imide (LiTFSI)—tetraglyme electrolyte as stated in Methods and the cells were charged by linear sweep voltammetry (LSV). As shown in Fig. 1a, the anodic current for oxidation reaction and gas evolution started at 3.9 V (vs. Li^+/Li , all potentials in the text below are versus Li^+/Li), which is consistent with the thermodynamic decomposition potential of Li_2CO_3 (3.82 V according to Eq. 1). A control experiment without Li_2CO_3 was carried out (Supplementary Fig. 3). The onset potential of electrolyte decomposition is at 4.3 V. The background current of carbon/ electrolyte oxidation at 3.8 V is 10-fold smaller than Li_2CO_3 decomposition (Fig. 1a) and there is no CO_2 or O_2 evolution. In Fig. 1a, a large amount of CO_2 and CO were identified as the gas products, which confirms the decomposition of Li_2CO_3 , consistent with the literature^{16,17}. According to the mass loading of the electrode (see Methods), ~60% of the preloaded Li_2CO_3 decomposed eventually. The ratio e^-/CO_2 for Fig. 1a is 2.1, close to $2e^-$ per CO_2 (Supplementary Table 1), suggesting it is an electrochemical process. The deviation is from the electrolyte electro-oxidation without producing CO_2 (Supplementary Fig. 3), which is consistent with the literature⁴¹. The molar flux of both CO_2 (denoted as \dot{n}_{CO_2}) and CO (denoted as \dot{n}_{CO}) follow the trend of the current during charging (equivalent to $\dot{n}_{\text{electron}}$) but they could derive from different processes because of the multisource of the CO_2 and CO evolution. Therefore, we mainly focus on the ratio CO_2/CO because it helps us to determine the mechanisms (Eqs. 1–3). The ratio CO_2/CO exhibits the comparison between Li_2CO_3 decomposition and other reactions because Li_2CO_3 decomposition does not form CO, as discussed later. The ratio CO_2/CO in Fig. 1a is 7.06 (Supplementary Table 2), which does not fit any reaction pathways proposed above. Due to the lack of O_2 evolution, Eq. (1a) could be excluded. The oxygen appears as singlet O_2 ($^1\text{O}_2$) instead of low-energy triplet O_2 ($^3\text{O}_2$), which will be discussed in detail later.

To further study the influence of electrode composition on the gas products, the same experiment was conducted using a Li_2CO_3 - Super P (4:1) composite electrode. As shown in Fig. 1b, similar gas species without O_2 were identified. Because the Li_2CO_3 -Super P (4:1) composite electrode contains more insulating Li_2CO_3 solid than that in Li_2CO_3 -Super P (1:1) electrode, leading to poor solid-solid contact, the charging current and consequent gas evolution in Li_2CO_3 -Super P (4:1) is one order of magnitude lower than those in Li_2CO_3 -Super P (1:1) electrode. If the CO_2 and CO came from a certain intermediate or a simple one-step reaction, the same ratio CO_2/CO would be observed. However, the ratio CO_2/CO varies with the electrode composition, from 7.06 to 9.82 (Supplementary Table 2). This result suggests that the Li_2CO_3 decomposition is a complicated multistep process, instead of a simple one-step reaction as proposed previously^{16,17}. Because Li_2CO_3 , the

carbon substrate, and the electrolyte all might contribute to CO_2 and CO evolution, it brings up the confusion about the source of CO_2 and CO , which is the key to addressing the reaction mechanisms.

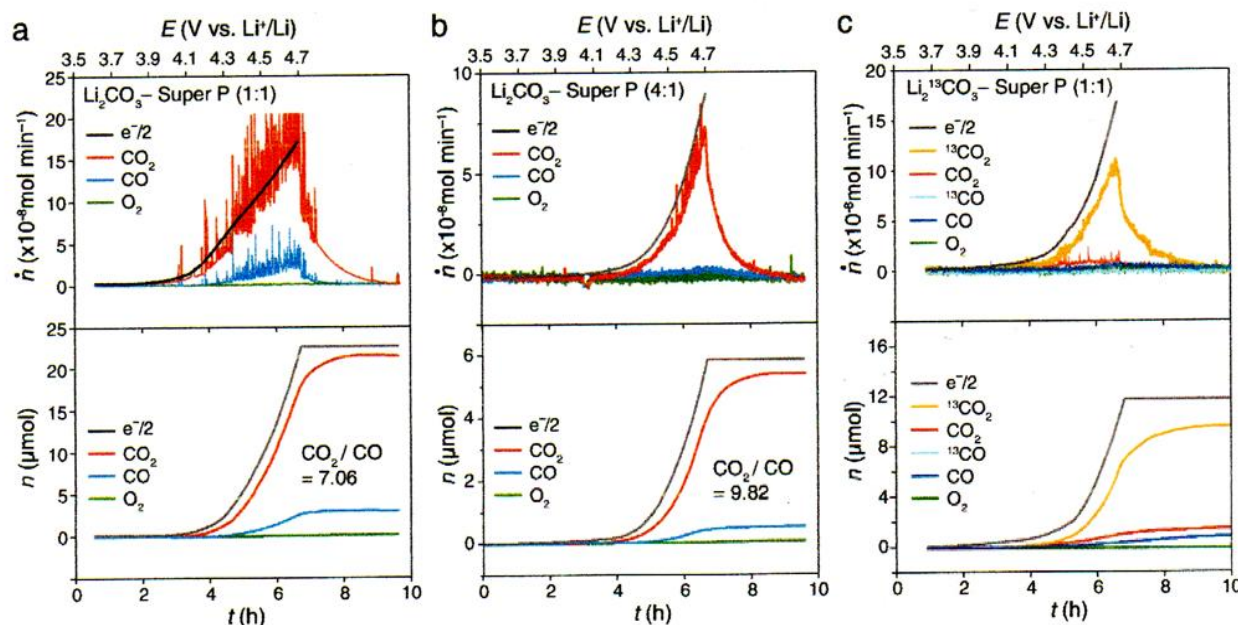


Fig. 1 / Gas evolution of oxidative decomposition of Li_2CO_3 and $\text{Li}_2^{13}\text{CO}_3$. The gas evolution during the charging process of the cells using **a** Li_2CO_3 -Super P (1:1), **b** Li_2CO_3 -Super P (4:1), **c** $\text{Li}_2^{13}\text{CO}_3$ -Super P (1:1) composite electrodes in 1M LiTFSI tetraglyme Ar flow rate: 0.5 mL min^{-1} . Sweep rate: 0.05 mV s^{-1} . The molar flux (top panel) of gas evolution was denoted as \dot{n} and the charging current is translated to $\dot{n}_{\text{electron}}$ and the cumulative mole (bottom panel) of the gas was denoted as n .


Gas products of $\text{Li}_2^{13}\text{CO}_3$ decomposition

The isotope-labeled $\text{Li}_2^{13}\text{CO}_3$ was used to identify the decomposition mechanisms of Li_2CO_3 . The Raman spectrum and XRD pattern of the $\text{Li}_2^{13}\text{CO}_3$ confirm its composition (Supplementary Fig. 4). The ^{12}C -impurity in $\text{Li}_2^{13}\text{CO}_3$ is determined by using a mass spectrometer (MS). The details are described in Methods—Isotope impurities. The $\text{Li}_2^{13}\text{CO}_3$ contains 15% isotope impurity of $\text{Li}_2^{12}\text{CO}_3$ (Supplementary Fig. 5), which would be subtracted from the MS results in the following experiments.

Figure 1c exhibits the gas evolution during the charging process of the cell with a $\text{Li}_2^{13}\text{CO}_3$ -Super P composite electrode. $\text{Li}_2^{13}\text{CO}_3$ was electro-oxidized and a large amount of $^{13}\text{CO}_2$ is identified, which is definitely from the $\text{Li}_2^{13}\text{CO}_3$ decomposition because both Super P carbon and electrolyte are unlabeled. No O_2 evolution is identified again. ^{13}CO was not observed as well, indicating that the $\text{Li}_2^{13}\text{CO}_3$ decomposed to merely $^{13}\text{CO}_2$ without ^{13}CO .

The decomposition of $\text{Li}_2^{13}\text{CO}_3$ (releasing $^{13}\text{CO}_2$) contributes 79% of the overall CO_2 and CO evolution and it is the dominant process during charging. Meanwhile, some CO_2 and CO from the inevitable decomposition of electrolyte and carbon substrate were identified during charging. The electrolyte/ carbon decomposition contributes to approximately one-fifth of total gas evolution (Supplementary Table 3), which is a high ratio of side reactions.

In the Li-CO_2 chemistry with lithium carbonate isotopically labeled with ^{13}C on an unlabeled carbon substrate (which we write here as ^{12}C for simplicity), $\text{Li}_2^{13}\text{CO}_3$ is posited to decompose together with the carbon substrate in the following reaction:



If it was the case, the ratio between $^{13}\text{CO}_2$ and $^{12}\text{CO}_2$ is expected to be about 2/1, but we find a ratio of 6.1/1 (Supplementary Table 4), much higher than 2/1 because ^{12}C does not transform to sufficient $^{12}\text{CO}_2$. This result suggests that the decomposition of the $\text{Li}_2\text{CO}_3\text{-C}$ electrode is a complicated reaction instead of a simple reaction with known stoichiometric numbers like Eq. (4). Therefore, the contribution of the C substrate during the charging process is the key to demystifying the reaction mechanisms.

Decomposition of ^{13}C -carbon substrate

To determine the contribution of carbon in this reaction, the same experiments were carried out again but by replacing the Super P carbon substrate with ^{13}C -carbon and leaving the lithium carbonate and electrolyte unlabeled. The ^{13}C -carbon contains 1.5% of ^{12}C impurity as shown in Supplementary Fig. 6. As shown in Fig. 2 and Supplementary Fig. 7, both $^{13}\text{CO}_2$ and ^{13}CO evolved during the charging process and the rest of CO_2 and CO evolution came from the decomposition of Li_2CO_3 and electrolyte. As the only source of ^{13}C -isotope, ^{13}C is oxidized to release both $^{13}\text{CO}_2$ and ^{13}CO during the charging process. The formation of ^{13}CO exhibits that the ^{13}C is oxidized incompletely like an incomplete combustion reaction. The ^{13}C substrate could be oxidized either electrochemically by potential or chemically by oxidative agents that are formed in the previous steps. If ^{13}C is oxidized electrochemically, the ratio $^{13}\text{CO}_2/^{13}\text{CO}$ would depend on the potential (Fig. 2). If ^{13}C is oxidized chemically by oxidative agents like $^1\text{O}_2$ and superoxide species, which are generated during the charging process, the electrode composition affects the ratio between $^{13}\text{CO}_2$ and ^{13}CO .

Impact of the potential on the decomposition of ^{13}C -carbon substrate

Due to the high equilibrium potential of Li_2CO_3 decomposition (3.82 V), the cell potential could affect the decomposition reactions and thus affect the formation of $^{13}\text{CO}_2$ and ^{13}CO at different potentials during the

charging process. Therefore, a cell with Li_2CO_3 -Super P composite electrode was charged with LSV from 4.3 to 4.7 V and the gas evolution was measured. The cell was rested for 4 h after reaching 4.3, 4.4, 4.5, 4.6, and 4.7 V, respectively, to obtain a low background of gas evolution. The cumulative molar of gas evolution at various potential stages is shown in Fig. 2. The amount of CO_2 from Li_2CO_3 decomposition increased when the potential increased. The higher the potential was, the more CO_2 evolved, in accord with the accelerating decomposition of Li_2CO_3 . Meanwhile, $^{13}\text{CO}_2$ and ^{13}CO evolved simultaneously and their amount increased together with the CO_2 evolution when the potential increased. Supplementary Fig. 7 shows the gas evolution at various stages of the charging process from 4.4 to 4.7 V. The amount of $^{13}\text{CO}_2$ and ^{13}CO evolution increased with the rising potential up to 4.7 V. This increase is probably because more singlet oxygen forms at a higher potential, which leads to more severe carbon and electrolyte degradation. Although both $^{13}\text{CO}_2$ and ^{13}CO increased, the ratio $^{13}\text{CO}_2/^{13}\text{CO}$ remains almost identical at these stages. This result suggests that the $^{13}\text{CO}_2$ and ^{13}CO likely originated from the same chemical reaction.

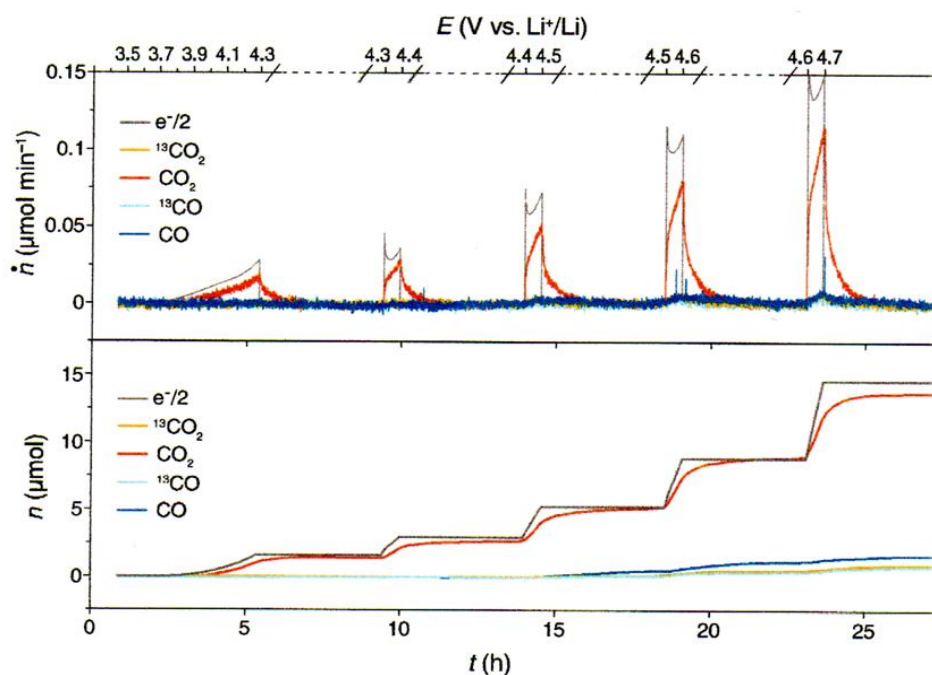


Fig. 2 | Potential-dependent CO_2 and CO evolution during the charging process. The gas evolution during the charging process of the cells using Li_2CO_3 - ^{13}C (1:1) composite electrode in 1M LiTFSI-tetraglyme. Sweep rate: 0.05mV s^{-1} . The cell rested for 4 h after reaching 4.3, 4.4, 4.5, 4.6, and 4.7 V, respectively. Ar flow rate 0.5mLmin^{-1} . The molar flux (top panel) of gas evolution was denoted as \dot{n} and the charging current is translated to $\dot{n}_{\text{electron}}$ and the cumulative mole (bottom panel) of the gas was denoted as n .

To check whether ^{13}C is oxidized to any solid by products, the cell was disassembled at the end of charging and the composite electrode was collected to further quantify the remained solid by-product of inorganic/organic carbon as described in Methods—Quantification of the solid byproducts. Neither $\text{Li}_2\text{ }^{13}\text{CO}_3$ (Supplementary Fig. 8a) nor organic ^{13}C -carbonates (Supplementary Fig. 8b) were detected in the charged electrode, indicating that the ^{13}C did not oxidize to any solid by-products, i.e., inorganic and organic carbonates. Only unlabeled inorganic Li_2CO_3 and organic carbonate were identified, which are from undecomposed Li_2CO_3 and electrolyte decomposition. The incomplete decomposition of Li_2CO_3 may be due to

the poor solid contact between the carbon substrate and Li_2CO_3 during the charging process. It is unlikely to decompose all Li_2CO_3 even up to 4.7 V, which is consistent with the literature⁴¹. Therefore, as only ^{13}CO and $^{13}\text{CO}_2$ and no ^{13}C -containing solid products are detected when using ^{13}C as the carbon substrate, the carbon substrate is only oxidized to gaseous carbon monoxide and carbon dioxide during charge in the presence of lithium carbonate and the 1M LiTFSI-tetraglyme electrolyte.

Previous results showed that the functional groups at the carbon surface dominated the decomposition of the carbon substrate⁴⁷. Therefore, the Raman and XPS spectra of ^{13}C and Super P are recorded to show their surface condition (Supplementary Fig. 9). D-band and G-band of ^{13}C were observed at 1289 and 1507 cm^{-1} , respectively, in the Raman spectrum (Supplementary Fig. 9a). Both D-band and G-band drift in the negative direction due to the isotope effect. The intensity of the D-band and G-band (ID/IG) typically represents the disorderliness and amounts of defects in the carbon structure. Here, ^{13}C and Super P carbon show the same ID/IG of 1.20, which indicates the same degree of disorderliness and a similar amount of defects from the surface of ^{13}C and Super P. Similar XPS spectra are shown in Supplementary Fig. 9b, confirming the similar surface groups of these two carbon substrates. Therefore, ^{13}C and Super P have similar surface functional groups and they are likely to exhibit similar behavior in this carbon decomposition on charge.

Impact of the ratio of Li_2CO_3 and carbon on the gas evolution

Although the ^{13}C carbon substrate oxidized to ^{13}CO and $^{13}\text{CO}_2$, its decomposition pathway is still ambiguous. It might be a pathway similar to the incomplete combustion reaction. Alternatively, ^{13}CO and $^{13}\text{CO}_2$ might be derived from a reaction intermediate with known structures like oxalate ($\text{C}_2\text{O}_4^{2-}$). To clarify the pathway, we studied the gas products of four Li_2CO_3 - ^{13}C composite electrodes with various mass ratios of $\text{Li}_2\text{CO}_3/^{13}\text{C}$ from 2:1 to 1:4 (Fig. 3). Overall, the carbon decomposition contributes to about 10% of the total gas evolution and the exact contribution depends on the composition of the electrodes (Supplementary Table 3). When the composite electrode contains less Li_2CO_3 , ratio $^{13}\text{CO}_2/^{13}\text{CO}$ decreases from 1.25 to 0.51 (Fig. 3h), indicating the extent of oxidation of ^{13}C is restricted by the amount of Li_2CO_3 in the composite electrodes. Otherwise, the ^{13}C would be completely oxidized to $^{13}\text{CO}_2$ instead of the mixture of $^{13}\text{CO}_2$ and ^{13}CO . This varying ratio $^{13}\text{CO}_2/^{13}\text{CO}$ confirms that the overall reaction is a multistep reaction, rather than forming a complex intermediate like $\text{C}_2\text{O}_4^{2-}$ which should give a certain ratio $^{13}\text{CO}_2/^{13}\text{CO}$ independent of the ratio of $\text{Li}_2\text{CO}_3/^{13}\text{C}$. The ^{13}C is highly likely to be oxidized by the oxidative intermediates from Li_2CO_3 decomposition. Therefore, as ratio $^{13}\text{CO}_2/^{13}\text{CO}$ varied with varying composition of the Li_2CO_3 - ^{13}C composite electrode, we argue that the amount of Li_2CO_3 present in the electrode, and thus the amount of oxidative intermediates from Li_2CO_3 decomposition, influences the decomposition route of the carbon substrate.

Oxidation of ^{13}C -carbon by $^1\text{O}_2$ and superoxide

Both $^1\text{O}_2$ and superoxide are reactive intermediates formed during the discharge and charging process in Li-air batteries, which could result in the decomposition of the carbon substrate^{48–52}. $^1\text{O}_2$ could attack the electrolytes and the electrodes as a strong oxidative species. Here, 9,10 dimethylantracene (DMA), a molecular trap for $^1\text{O}_2$, is used to identify the $^1\text{O}_2$ during electrochemical oxidation for the Li_2CO_3 -C composite electrodes (see Methods—Identification of $^1\text{O}_2$). When $^1\text{O}_2$ forms, it rapidly reacts with DMA to form DMAO₂, which could be identified in the ¹H NMR spectrum. Here, at the end of the charging process, the electrolyte with DMA in the cell was extracted and its ¹H NMR spectrum (Supplementary Fig. 10) shows that DMAO₂ has formed, which confirms the formation of $^1\text{O}_2$ during the charging process. Once $^1\text{O}_2$ forms, $^1\text{O}_2$ attacks carbon and releases ^{13}CO and $^{13}\text{CO}_2$.

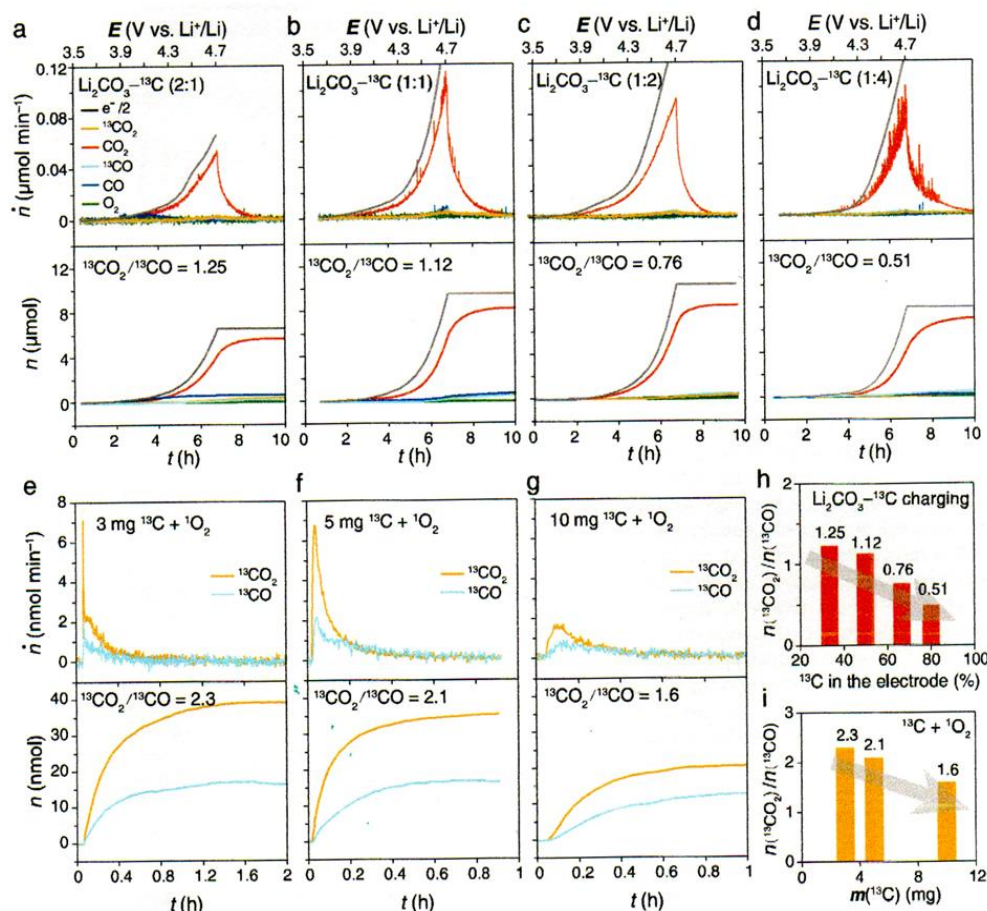


Fig. 3 | Incomplete oxidation of ^{13}C -carbon by singlet O_2 to form ^{13}CO and $^{13}\text{CO}_2$. a–d The gas evolution during the charging process of the cells using the Li_2CO_3 - ^{13}C composite electrodes with various mass ratios of $\text{Li}_2\text{CO}_3/^{13}\text{C}$, a 2:1, b 1:1, c 1:2, d 1:4 in 1M LiTFSI-tetraglyme. e–g $^{13}\text{CO}_2$ and ^{13}CO evolution of the ex situ chemical reaction between singlet O_2 and ^{13}C -carbon in tetraglyme solution. 22mg KO_2 powder was mixed with e 3mg, f 5mg, g 10 mg of ^{13}C -carbon, respectively, and then 1mL of LiTFSI-tetraglyme (4M) was added to react with KO_2 to form singlet O_2 . The comparison of ratio $^{13}\text{CO}_2/^{13}\text{CO}$ in (h) ex situ chemical reaction for (e–g) and i charging process for (a–d).

Here, to study the contribution of $^1\text{O}_2$ and KO_2 to carbon decomposition, $^1\text{O}_2$ and KO_2 were respectively used to react with ^{13}C as ex situ chemical experiments. $^1\text{O}_2$ is produced from the disproportionation of superoxide species⁴⁷ (The reaction between KO_2 and Li^+ in this work). More details are described in Methods—Chemical experiments between reactive oxygen species and carbon. The gas evolutions of $^{13}\text{CO}_2$, ^{13}CO , $^{12}\text{CO}_2$, and O_2 in the reaction between $^1\text{O}_2$ and ^{13}C are shown in Fig. 3e–g and Supplementary Fig. 11. Figure 3e–g show both ^{13}CO and $^{13}\text{CO}_2$ evolution, which confirms the incomplete oxidation of ^{13}C -carbon by $^1\text{O}_2$. The formation efficiency of $^1\text{O}_2$ by disproportionation in solution is low, therefore, most O_2 is released as $^3\text{O}_2$ (Supplementary Fig. 11). Because $^1\text{O}_2$ is formed in the electrolyte solution rather than at the surface of ^{13}C , fresh $^1\text{O}_2$ is more likely to attack the electrolyte than the ^{13}C , forming a large amount of CO_2 . In addition, because a large amount of carbon makes the suspension viscous, the total amount of ^{13}CO and $^{13}\text{CO}_2$ slightly

decreased with the increase of ^{13}C . When the amount of ^{13}C increased, more ^{13}CO formed and the ratio $^{13}\text{CO}_2/^{13}\text{CO}$ decreased (Fig. 3i and Supplementary Table 5). Both the in situ electrochemical charging experiments (Fig. 3h) and ex situ chemical experiments (Fig. 3i) show the same decreasing trend of ratio $^{13}\text{CO}_2/^{13}\text{CO}$ with the increase of the amount of ^{13}C relative to $^1\text{O}_2$ or Li_2CO_3 .

On the other hand, to further exclude the contribution from superoxide species, the same chemical experiments were carried out but replaced $^1\text{O}_2$ with O_2 (sol). KO_2 was dissolved in tetraglyme and crown ether was added to maximize the concentration of the O_2^- (sol) in the solution. As shown in Supplementary Fig. 12, only ^{13}CO but no $^{13}\text{CO}_2$ was identified, which suggests that O_2^- (sol) is incapable to oxidize ^{13}C to $^{13}\text{CO}_2$. In summary, the detected ^{13}CO and $^{13}\text{CO}_2$ come from the side reaction of $^1\text{O}_2$ attacking the ^{13}C substrate (Eq. 6). Herein, we simulate the chemical reaction between $^1\text{O}_2$ and ^{13}C without applying potential, however, the potential applied in the charging process could make the real side-reaction more complicated. More $^1\text{O}_2$ might be produced at a higher potential. It is noted that oxygenated byproducts from chemical reactions with $^1\text{O}_2$ could first be produced and then electrooxidatively decomposed^{48,49}.

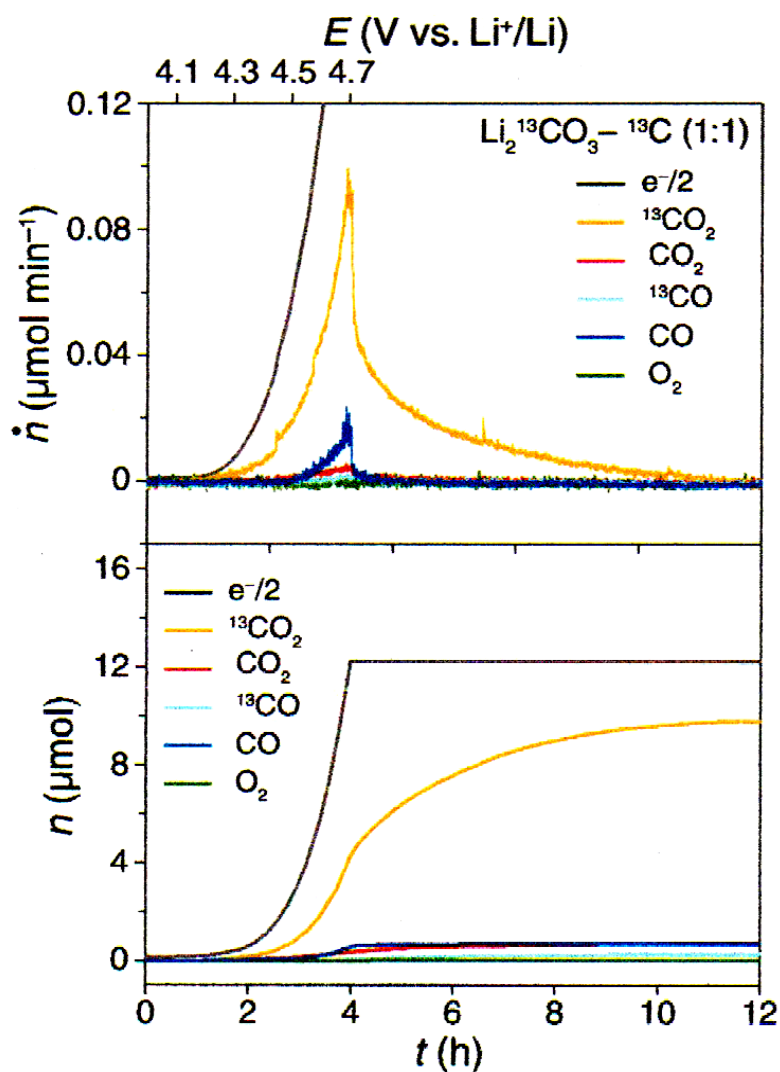


Fig. 4 / The gas evolution of the electrolyte decomposition. The gas evolution during the charging process of the cells using $\text{Li}_2\ ^{13}\text{CO}_3\text{-}^{13}\text{C}$ -carbon (1:1) composite electrode in 1MLiTFSI-tetraglyme. Ar flowrate: 0.5 mL min^{-1} . Sweep

rate: 0.05 mV s^{-1} . The molar flux (top panel) of gas evolution was denoted as \dot{n} and the charging current is translated to $\dot{n}_{\text{electron}}$ and the cumulative mole (bottom panel) of the gas was denoted as n . The unlabeled CO_2 and CO are contributed by electrolyte decomposition.

The CO and CO_2 evolution of electrolyte decomposition

The electrolyte decomposition during the oxidation of Li_2CO_3 on charge is inevitable and should not be ignored. A cell with $\text{Li}_2^{13}\text{CO}_3\text{-}^{13}\text{C}$ composite electrode was charged to quantify the contribution from electrolyte degradation (Fig. 4). Because the entire composite electrode is labeled with ^{13}C isotope, the $^{12}\text{CO}_2$ must come from the decomposition of the tetraglyme electrolyte. Figure 4 shows that $^{12}\text{CO}_2$ and ^{12}CO from the electrolyte decomposition contribute $\sim 12\%$ to the total gas evolution (Supplementary Table 6). The ratio between carbon dioxide species ($^{12}\text{CO}_2 + ^{13}\text{CO}_2$) and carbon monoxide species ($^{12}\text{CO} + ^{13}\text{CO}$) is 7.76, which is in accord with the ratio CO_2/CO of 7.06 in the $\text{Li}_2\text{CO}_3\text{-Super P (1:1)}$ composite electrode, as stated in Supplementary Table 2.

As discussed above, the decomposition of Li_2CO_3 and carbon substrate contributes to 79% and $\sim 10\%$, respectively, of the total gas evolution. The side-reactions of carbon depend on the electrode composition because this charging process highly depends on the solid-solid contact between Li_2CO_3 and carbon substrate. The exact ratios of decomposition of individual components were not completely identical in each experiment because the nature of Li_2CO_3 decomposition is based on the solid-solid contact. At some contacting points, the charging process will stop due to the large overpotential caused by the restricted solid-solid contact. The sum of gas evolution from Li_2CO_3 , carbon, and electrolyte is $\sim 100\%$, which confirms the reliability of individual measurements.

Although an important consideration, full understanding of electrolyte decomposition is not our focus in this work. Therefore, to ensure that it does not affect the major gas evolution from Li_2CO_3 and C, we quantified the gas by-products and solid by-products from the electrolyte decomposition without further analyzing the liquid byproducts dissolved in the solvent. The solid by-products, like Li_2CO_3 and organic carbon residuals in the composite electrode at the end of the charge, were quantified respectively. As shown in Supplementary Fig. 13, approximately one-third of $\text{Li}_2^{13}\text{CO}_3$ is unreacted and remained in the electrode and a trace amount ($< 0.1 \mu\text{mol}$) of organic carbonate were identified. This result indicates that there is no exchange of $^{12}\text{C}/^{13}\text{C}$ between the electrolyte and $\text{Li}_2\text{CO}_3/\text{C}$.

Electrochemical vs. chemical pathways of Li_2CO_3 decomposition Here our results show that Li_2CO_3 decomposition in the ether-based electrolyte is mainly an electrochemical process, which is in good agreement with Kaufman et al.³³, but Freiberg et al claimed that Li_2CO_3 decomposition was a chemical process in LiPF_6 carbonate-based electrolyte and it was induced by water⁴¹. They argued that the electrolyte was oxidized and decomposed on high potential and it formed some proton-derivatives which chemically react with Li_2CO_3 to

evolve CO_2 . To study the reasons of these contradicting results, we conducted a series of comparative experiments. Firstly, to avoid the direct participation of water in Li_2CO_3 decomposition, we carried out a chemical reaction between the commercial Li_2CO_3 and 1M LiTFSI tetraglyme electrolyte with 1000 ppm and 5000 ppm H_2O , respectively, and the gas evolution was recorded. The result in Supplementary Fig. 14 indicates that no CO_2 and O_2 were detected even if there were lots of protons (from water) in the electrolyte. Then, to check the impact of potential, a cell with blank carbon (Super P or ^{13}C) electrode without Li_2CO_3 but with 1000 ppm of H_2O in the electrolyte and the gas evolution was recorded, Supplementary Fig. 15. No O_2 and CO_2 evolved during the charging process below 4.7 V. Interestingly, in the presence of 1000 ppm H_2O , the onset potentials of electrolyte decomposition drifted to a lower potential of 3.8 V, compared with 4.1 V without H_2O . This result implies that H_2O encourages the electro-oxidation of the electrolyte but there is still no gas evolution below 4.5 V.

Learning from Freiberg's work, we decomposed Li_2CO_3 without direct electric contact to confirm the chemical mechanism⁴¹. Briefly, an extra Celgard membrane was placed between Li_2CO_3 powder and the blank carbon composite electrode to separate them. On one hand, the Li_2CO_3 cannot be electro-oxidized due to the lack of direct electronic contact with the carbon electrode. On the other hand, the porous Celgard membrane allows the electrolyte decomposition byproducts that form at the carbon composite electrode to diffuse across the Celgard and react with Li_2CO_3 .

For comparison, in the LiPF_6 -ethylene carbonate (EC)/ethyl methyl carbonate (DMC) electrolyte, the same setup was used but the gas evolution was analyzed at the end of the charging process due to the volatility of the EMC. Because the Li_2CO_3 is separated from the carbon electrode, it cannot be electro-oxidized. However, a large amount of CO_2 evolution was identified (Fig. 5a) above 4.3 V, suggesting the chemical decomposition of Li_2CO_3 by the electrolyte decomposition byproducts at high potential. This result is consistent with Freiberg's work⁴¹. The ratio e^-/CO_2 is 2.20, in good agreement with the literature⁴¹ but it does not mean that Li_2CO_3 is electro-oxidized via a 2-e process. Instead, the electrolyte decomposition is likely to produce active H^+ at a ratio e^-/H^+ of 1 and the H^+ reacts with Li_2CO_3 to release CO_2 at a ratio H^+/CO_2 of 2⁴¹. Therefore, here the ratio e^-/CO_2 is just used for comparison between these four cells. Here, the chemical pathway does not take place until a high potential over 4.3 V when the electrolyte was electro-oxidized first. For comparison, the CO_2 evolution in the charging process starts from ~3.9 V (Figs. 1–3), which is too low to electro-oxidize the electrolyte. Therefore, the Li_2CO_3 decomposition at low potential <3.9 V is dominated by the electrochemical pathway, instead of by a chemical pathway induced by electrolyte degradation by-products.

On the contrary, the same experiment but with LiTFSI-tetraglyme electrolyte shows little CO_2 evolution (Fig. 5b), which makes a sharp comparison to the $\text{LiPF}_6\text{-EC/EMC}$ electrolyte. In LiTFSI-tetraglyme electrolyte, CO_2 evolved from 4.3 V, indicating the decomposition of electrolytes at high potential could induce the chemical decomposition of Li_2CO_3 . However, the ratio e^-/CO_2 is 12.29, much higher than that in $\text{LiPF}_6\text{-EC/EMC}$. In addition, the total amount of CO_2 is as low as $0.4 \mu\text{mol}$, <2% of the CO_2 evolution in the Super P- Li_2CO_3 electrode, Fig. 1a. This distinct comparison indicates that the reaction mechanisms of Li_2CO_3 decomposition are completely different in $\text{LiPF}_6\text{-EC/EMC}$ and LiTFSI-tetraglyme electrolytes. The chemical pathway proposed by Freiberg is not applicable for tetraglyme-based electrolytes. The difference is due to either the Li salts or the solvents

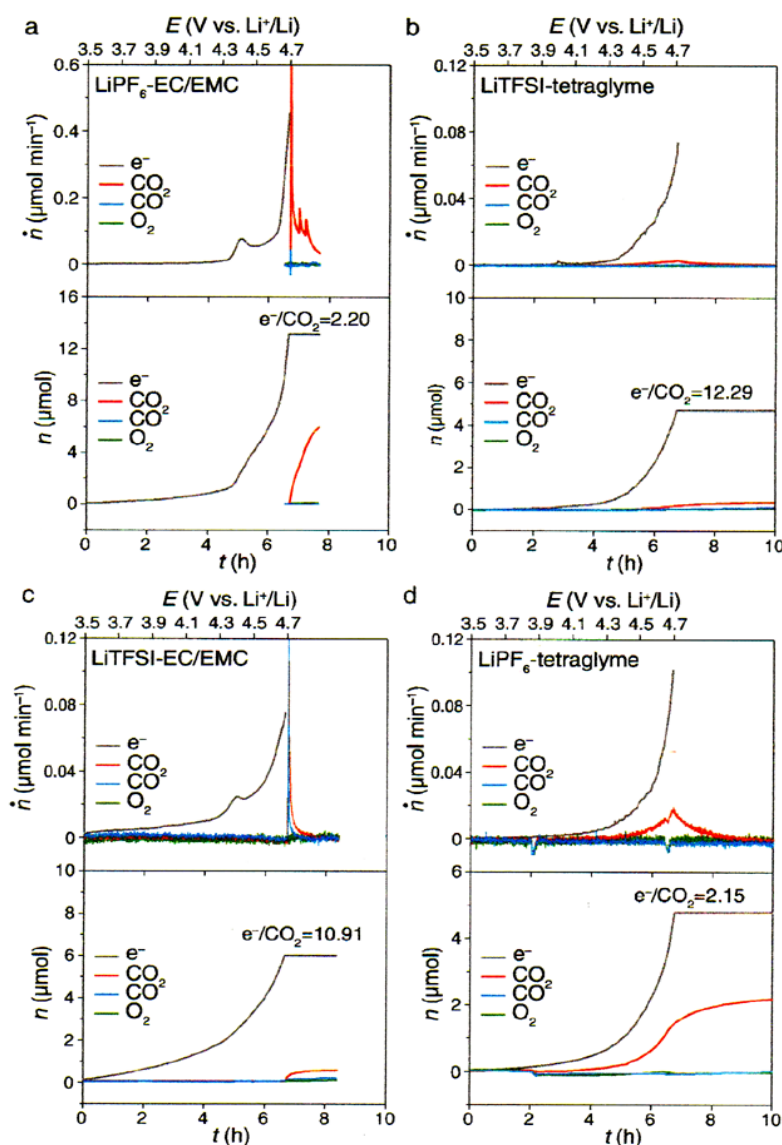


Fig. 5 / Impact of electrolyte salts and solvents on the gas evolution of chemical decomposition of Li_2CO_3 . The gas evolution during the charging process of the cells using Super P-PTFE composite electrodes without direct contact of Li_2CO_3 in (a) 1M $\text{LiPF}_6\text{-EC/EMC}$, (b) 1M LiTFSI-tetraglyme, (c) 1M LiTFSI-EC/EMC, and (d) 1M $\text{LiPF}_6\text{-tetraglyme}$. 20mg of commercial Li_2CO_3 was separated from the Super P-PTFE

To find out whether the Li salts or the solvents make the difference, the salts were exchanged in these electrolytes and LiTFSIEC/ EMC and LiPF₆-tetraglyme were used, Fig. 5c and d. Interestingly, the LiPF₆-tetraglyme shows much CO₂ evolution similar to LiPF₆-EC/ EMC. Meanwhile, LiTFSI-EC/EMC shows little CO₂ evolution similar to LiTFSI-tetraglyme. The cells using LiPF₆ salt show a large amount of CO₂ evolution. The electrolytes used in this work were all dried and the water concentrations were below 4 ppm (Karl-Fischer titration). Therefore, this chemical mechanism could be due to the LiPF₆ salt itself or its impurities because LiPF₆ is difficult to purify⁵³. Freiberg et al. also proposed that the chemical pathway involving LiPF₆ salt⁴¹. In the rest of this work, we used LiTFSI in tetraglyme as the electrolyte, thus excluding any possible effects of LiPF₆ on our results. As little CO₂ was evolved in the Celgard-separated experiment with LiTFSI-based electrolytes, our results provide evidence that Li₂CO₃ decomposition in LiTFSI-tetraglyme electrolytes is dominated by an electrochemical rather than chemical process.


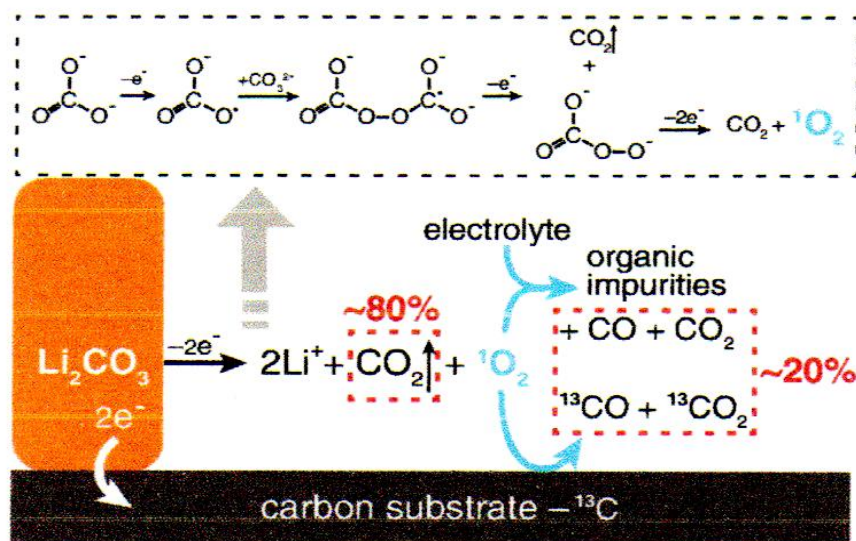


Fig. 6 / Schematics of the Li₂CO₃ decomposition on the charging process. Li₂CO₃ is electro-oxidized to form CO₂ and singlet O₂ (¹O₂). A possible pathway is proposed in the dash line box. ¹O₂ is highly reactive and it attacks the electrolyte and the carbon substrate to form carbon monoxide and carbon dioxide, which contribute to ~20% of the overall gas evolution.

We propose the following reactions for the electrochemical decomposition of Li₂CO₃ on carbon substrates:



Li_2CO_3 is oxidized at high potentials to form CO_2 and aggressive $^1\text{O}_2$ (Eq. 5), Fig. 6. $^1\text{O}_2$ attacks carbon substrate (Eq. 6) and electrolyte (Eq. 7) simultaneously like incomplete combustion reactions, leading to further side reactions forming CO_2 and CO . It should be noted here, Eq. (7) is just a schematic equation instead of a proper stoichiometric equation for an elementary reaction because we do not completely know all byproducts from electrolyte decomposition. The exact ratio CO_2/CO depends on the ratio between formed $^1\text{O}_2$, the carbon substrate/electrolyte, namely the electrode composition, but not on the cell potentials. Although the carbon substrate is eventually oxidized to CO_2 and CO , the carbon does not directly participate in the electrooxidation of Li_2CO_3 as has been proposed in the literature²⁸. As we mentioned above, the Eq. (2) could be recognized as a combination of Eq. (5) and Eq. (6) when x is equal to zero in Eq. (6). In this case, the reactive intermediate $^1\text{O}_2$ reacts with carbon to produce only CO_2 instead of a mixture of CO_2 and CO . However, our chemical reaction between $^1\text{O}_2$ and ^{13}C shows both $^{13}\text{CO}_2$ and ^{13}CO evolution (Supplementary Fig. 11). If a highly reactive intermediate other than $^1\text{O}_2$ forms in the Li_2CO_3 decomposition and rapidly attacks carbon to just CO_2 , Eq. (2) could establish and contribute to a parallel pathway with Eq. (1) in Li_2CO_3 decomposition. However, there is so far no evidence of such a highly reactive intermediate.

Overall, during the charging process of the cell with a Li_2CO_3 -carbon composite electrode in LiTFSI-tetraglyme electrolyte, Li_2CO_3 decomposition contributes the major CO_2 evolution (~80%), and the carbon substrate and electrolyte decomposition share the rest ~20% of gas evolution. Therefore, in the charging process of Li-air batteries and Li- CO_2 batteries, the decomposition of carbon substrate and the electrolyte is inevitable and contributes to a significant amount of CO_2 and CO unless the $^1\text{O}_2$ can be suppressed.

Implications for batteries

Although Li_2CO_3 can be decomposed during the charging process, it is accompanied by severe side reactions by $^1\text{O}_2$ (~20% of the total gas evolution) and leads to deterioration of cell performance. Here, we focus on Li-air and Li- CO_2 batteries. In Li-air batteries, Li_2CO_3 is a major by-product and it passivates the electrode surface and kills the cells, which brings us to a dilemma. On one hand, if Li_2CO_3 is not decomposed during the charging process, Li_2CO_3 will rapidly accumulate during cell cycling and thus completely passivate the electrode. On the other hand, if Li_2CO_3 is decomposed during the charging process, it results in more side-reactions and thus accelerates cell deterioration. This effect is more significant in Li- CO_2 batteries because Li_2CO_3 and carbon form are supposed to be the main discharge products. Therefore, a reversible decomposition of Li_2CO_3 and carbon is desired in the following charging process^{16,17}. However, during the charging process, the discharge reaction cannot be completely reversed because the carbon does not directly participate in the Li_2CO_3 decomposition reactions. The carbon substrate is oxidized by the $^1\text{O}_2$ intermediate to CO_2 and CO . Meanwhile, the aggressive $^1\text{O}_2$ attacks the electrolyte, leading to the depletion of the electrolyte and consequently cell failure. If the electrolytes and salts in the cells are sufficiently stable, e.g., solid-state electrolyte, the molten-salt electrolyte of $\text{LiNO}_3\text{-KNO}_3$, etc, the side-reactions with electrolyte could be avoided and $^1\text{O}_2$ quenches to $^3\text{O}_2$. Recently, Zhang's group observed the O_2 evolution when charging Li_2CO_3 in the cell using a solid-state electrolyte⁵⁴. Due to the stability of inorganic solid-state electrolyte, $^1\text{O}_2$ had nothing

to attack and eventually was quenched to $^3\text{O}_2$. However, even in this case, the $^1\text{O}_2$ would oxidize the carbon substrate and thus the cell deterioration cannot be completely inhibited.

Therefore, the key to pursuing a better charging process is to design a catalyst that suppresses the formation of $^1\text{O}_2$ rather than simply facilitates the kinetics of Li_2CO_3 decomposition and thus decreases the overpotentials. For instance, some redox mediators (RM) with moderate O_2 binding energy could be applied to inhibit forming $^1\text{O}_2$ and encourage $^3\text{O}_2$ evolution by replacing the $^1\text{O}_2$ precursor (e.g. CO_4^{2-}) with a low-energy RM-involved intermediate, just like the way 2,5-di-tert-butyl-1,4-benzoquinone does to O_2^{-55} . Alternatively, some solid catalysts with suitable O_2 binding energy could bind $^1\text{O}_2$ precursor (the key reaction intermediate of Li_2CO_3 decomposition) in order to lower the energy and stabilize the precursor before it transforms to $^1\text{O}_2$. The ratio of $^1\text{O}_2$ in the final product will decrease when the energy of the $^1\text{O}_2$ precursor decreases.

Very recently, Hu's group used operando electron paramagnetic resonance to show that Co_3O_4 inhibited the $^1\text{O}_2$ formation during the charging process of Li- O_2 cells⁵⁶. Here, we added some Co_3O_4 nanoparticles to the Li_2CO_3 -Super P composite electrode and then charged the electrode. As shown in Supplementary Fig. 16a, some O_2 was identified during the charging process. While the control experiment of charging the Co_3O_4 electrode itself without Li_2CO_3 exhibits no O_2 evolution, Supplementary Fig. 16b. This result confirms that the Co_3O_4 catalyst successfully interacts with the precursor of forming $^1\text{O}_2$ during the Li_2CO_3 decomposition and thus suppresses $^1\text{O}_2$ formation. On the other hand, the CO evolution with Co_3O_4 is only half of that without Co_3O_4 , whereas similar CO_2 evolutions were identified in both experiments. Because CO is from side-reactions of $^1\text{O}_2$ attacks electrolyte/ carbon substrate, decreased CO evolution confirms that $^1\text{O}_2$ formation was partially inhibited and thus fewer side-reactions of $^1\text{O}_2$ attacking the carbon substrate and the electrolyte were detected than the counterpart without Co_3O_4 , Supplementary Fig. 17. Our results are in good agreement with Hu's group results⁵⁵. Although the $^1\text{O}_2$ formation and CO evolution cannot be completely inhibited, the Co_3O_4 does make some effects by stabilizing the reaction intermediates of forming $^1\text{O}_2$ and thus encouraging the evolution of $^3\text{O}_2$. This example confirms the feasibility of this strategy to promote the Li_2CO_3 decomposition with less parasitic $^1\text{O}_2$, however further studies are needed to look for more effective catalysts to avoid the side-reaction caused by $^1\text{O}_2$.

To explore the decomposition mechanisms of the Li_2CO_3 and clarify the role of carbon substrate in the charging process of Li_2CO_3 - carbon composite electrodes in LiTFSI-tetraglyme electrolyte, we did a set of in situ DEM-GC experiments with the ^{13}C isotope-labeled composite electrodes to systematically isolate each component of the cell. The gas evolution during the charging process, including CO, CO_2 , ^{13}CO , $^{13}\text{CO}_2$, and O_2 was quantified. Li_2CO_3 decomposed to release CO_2 at an onset potential of 3.8 V mainly via an electrochemical mechanism. The chemical mechanism of Li_2CO_3 decomposition in literature could take place in the presence of LiPF_6 due to LiPF_6 itself or its impurities. Carbon substrate did not directly participate in the decomposition of Li_2CO_3 , that is to say, carbon did not react with Li_2CO_3 in a single step to form CO_2 as desired. On the contrary, this process is a multistep reaction. In the first step, Li_2CO_3 was oxidized to CO_2 and $^1\text{O}_2$. Then, the $^1\text{O}_2$ simultaneously oxidized the carbon substrate and electrolyte to form CO_2 and CO as

gaseous side products. Approximately 80% of the net/cumulative CO₂ evolution is contributed by the Li₂CO₃ decomposition and the rest ~20% is contributed by the decomposition of the carbon substrate and the electrolyte, which cannot be ignored in batteries, particularly in Li- CO₂ batteries. In this work, we clarify the reaction mechanisms of the Li₂CO₃ decomposition during the charging process and exhibit the role of carbon in this process. This finding establishes a detailed picture of the decomposition pathways of Li₂CO₃ which enables strategy for the design of highly efficient cathode catalysts for Li-air and Li-CO₂ batteries.

Methods

Materials

Lithium carbonate (Li₂CO₃), potassium superoxide (KO₂), lithium bis(trifluoromethane)sulfonamide (LiTFSI), 9,10-dimethylantracene (DMA), and Co₃O₄ were purchased from Sigma-Aldrich. Li₂ ¹³CO₃ and ¹³C were purchased. Tetraethylene glycol dimethyl ether (tetraglyme), ethylene carbonate (EC), and methyl ethyl carbonate (EMC) were purchased from the TCI Chemical. Tetraglyme was distilled under vacuum and dried with activated molecular sieves (4 Å). Lithium hexafluorophosphate (LiPF₆), ferrous sulfate (FeSO₄), phosphoric acid (H₃PO₄), acetic acid, and hydrogen peroxide (H₂O₂) were purchased. Lithium iron phosphate (LFP) was purchased. Dimethyl sulfoxide-d₆ (DMSO-d₆) and 18-crown-6 were purchased. Argon (N5 grade) and 10 % Ar-O₂ (N5 grade) were obtained from. Polytetrafluoroethylene emulsion (PTFE) was purchased from Innochem. Celgard separator (25 µm thickness, Celgard), glass fiber separator (GF/F, Whatman), and Super P carbon (Timcal) were also purchased.

Preparation of the composite electrodes

The blank carbon electrode, Li₂CO₃-carbon composite, and Li₂CO₃- Super P-Co₃O₄ composite (1:1:0.5) electrodes were prepared as described in literature^{9,28,56}. Briefly, a certain amount of Super P, Li₂CO₃, and Super P carbon or Li₂CO₃, Super P and Co₃O₄, and PTFE were mixed and the mixture was ball milled overnight. The mass ratio of active material and binder PTFE is 10:1. A certain amount of well mixed powder was weighed and absolute ethanol was added to obtain a slurry. The slurry was cast onto pre-washed stainless steel (SS) mesh (100 mesh) and the electrodes were dried under vacuum at 120 °C overnight. The mass loading is 5mg per electrode. For instance, a Super P- Li₂CO₃ (1:1) composite electrode contains 2.27mg Super P, 0.46mg PTFE, and 2.27mg Li₂CO₃ (equivalent to 30.7 µmol). For the ¹³C-isotope-labeled electrodes, the Li₂CO₃ and the Super P were replaced with the Li₂ ¹³CO₃ and ¹³C carbon, respectively. The ¹³C isotope labeled composite is only obtained by grinding because the ¹³C-isotope-labeled substance is too expensive.

Preparation of the LFP electrode

80mg LFP powder, 10mg Super P, and 100mg PTFE suspension (10%) were prepared. Firstly, 80mg LFP and Super P were ground in a mortar to ensure that the LFP and Super P were evenly mixed. 0.1 mL of ethanol was dropped into the mixed powder to wet it and then the PTFE suspension was added to the mixed powder. After LFP-Super P and PTFE were mixed evenly, it was rolled several times with a roller. The final thickness of the electrode is 0.8mm. The LFP electrode was punched into 12–25mm diameter and then soaked

in a solution (7.2mL 30% H_2O_2 and 3 mL acetic acid in 500mL H_2O) for 30min to precharge the LFP. The precharged LFP electrodes were rinsed with water five times to completely remove the residual H_2O_2 and acetic acid. Finally, the treated LFP electrodes were dried in a vacuum oven overnight and transferred to a glove box for later use.

Potential calculation

Ag wire was used as a pseudo-reference electrode in a three-electrode cell. We immersed the Ag wire in 1M LiTFSI tetraglyme electrolyte with O_2 to stabilize the potential of the Ag wire. A three-electrode cell with a LFP working electrode was charged and discharged in 1M LiTFSI tetraglyme using this Ag wire as the reference electrode. The equilibrium potential of LFP was 0.5 V versus Ag wire. Considering the potential of LFP versus Li^+/Li is 3.45 V, the potential of the Ag wire is 2.95 V versus Li^+/Li . Therefore, the potentials versus Li^+/Li of the experiments in 1M LiTFSI-tetraglyme could be calculated. All potentials in this manuscript are versus Li^+/Li without further notice.

DEMS-GC setup

A differential electrochemical mass spectrometer (DEMS, Prima BT, Thermo Scientific Ltd.) was coupled with a gas chromatograph (GC, Hope Ltd.) in parallel (Supplementary Fig. 1). The GC is equipped with a TCD and an FID detector (including a CO_2/CO converter). The DEMS cell is based on a customized Swagelok design. It was assembled and charged/discharged in the Ar-filled glove box. The Ar carrier gas carried the evolved gas in the cell into DEMS and GC simultaneously. The typical flow rate of Ar carrier gas is 0.5 mL min^{-1} and the sweep rate for LSV is 0.05 mV s^{-1} . The time resolutions of DEMS and GC are 10 seconds and 5min, respectively. The general gas evolution in chemical reactions was examined by the mass spectrometer (MS, Prima BT) itself.

Experiments of Li_2CO_3 with 1000/5000 ppm H_2O in 1M LiTFSI tetraglyme electrolyte. Firstly, 1000 ppm and 5000 ppm H_2O were added to the 1M LiTFSI tetraglyme electrolyte, respectively and the water concentration in the electrolyte was quantified by a Karl Fischer titrator (Mettler Toledo). Then, the gas analysis was conducted in a MS. Generally, 100mg commercial Li_2CO_3 was added to a vial that was connected to a MS. After passing in the carrier gas for a while to obtain a steady baseline, 1mL electrolyte with H_2O was added to the vial and it was stirred for several hours. The gas evolution was quantified by a MS.

Quantification of gas evolution during the charging process

The composite electrodes were charged in a homemade differential electrochemical mass spectrometry cell. A piece of precharged LiFePO_4 served as the counter electrode and a piece of silver wire served as the reference electrode. 0.2mL of 1M LiTFSI-tetraglyme served as the electrolyte. The water content of the electrolyte was <4 ppm tested by Karl Fischer moisture titrator. To study the impact of the potential on the charging process, the composite electrodes were charged using linear sweep voltammetry (LSV) with a sweep rate of 0.05 mVs^{-1} . Due to the stability window (4.8 V) of the tetraglyme-based electrolyte, the cell potential

was cut off at 4.7 V. Argon was served as the carrier gas and its flow is 0.5ml/min. The gas evolution was examined by a magnet sector mass spectrometer (Prima BT, Thermo Scientific Ltd.).

For the experiments for the chemical route, the Li_2CO_3 was deliberately separated from the Super P-PTFE composite electrolyte to allow the electrolyte decomposition byproduct to decompose Li_2CO_3 chemically. Twentymilligrams of commercial Li_2CO_3 was weighed and dusted to the top of the separator. A piece of Celgard separator (25 μm thickness) was stacked on the Li_2CO_3 and then a Super P-PTFE composite electrode is stacked on the Celgard. The composite electrode was electronically isolated from Li_2CO_3 by the Celgard separator. For the 1MLiTFSI-tetraglyme electrolyte, the cell was charged to 4.7 V and the gas evolution was recorded. For the control experiment with EC/ EMC electrolyte, due to the volatile electrolyte, the cell was not purging with Ar carrier gas during the entire charging process. The gas evolution in the headspace was purged with Ar at the end of the charging process to quantify the CO_2 evolution during the entire charging process. A homemade in-line cold trap (-25°C) was applied to condense the evaporated EMC to minimize the background noise caused by EMC.

Quantification of CO

The mass-to-charge (m/z) ratio of 28 could be contributed by CO, N_2 , and the fragment of CO_2 . To exclude the contribution of the N_2 , the gas inlet of the DEMS was placed inside an Ar-filled glove box as shown in Supplementary Fig. 1 and the DEMS experiments were conducted inside the glove box at $25 \pm 2^\circ\text{C}$ to minimize the impact of N_2 leakage. The $m/z = 28$ fragment from CO_2 was calibrated with a calibration gas of 1% CO_2 –99% Ar using DEMS. The intensity of the $m/z = 28$ signal is 6.5% of the $m/z = 44$ signal, which is subtracted from the concentration of CO in the calculation. This ratio ($m/z=28/m/z = 44$) depends on many factors, such as electron voltage, emission current of the filaments, etc. Therefore, this ratio needs to be calibrated for individual MS. A calibration gas of 0.1% CO–99.9% Ar was used for calibration.

The CO evolution during the charging process was parallelly quantified by a GC with a TCD and a FID detector (including a CO_2/CO converter). A FID detector was used to quantify the CO and 1000 ppm CO equals an area of 130mVs in GC. Thus we could use these results as a reference and qualify the amount of CO in all experiments.

Quantification of the solid byproducts

The solid Li_2CO_3 and organic carbon in the composite electrodes were quantified as reported previously⁵⁷. An electrode was placed in a vial that is connected to a MS and 0.5ml of H_3PO_4 (2 M) was injected into the vial to react with Li_2CO_3 to form CO_2 . The CO_2 evolution was quantified by MS. Afterward, Fenton solution (400 μL FeSO_4 +50 μL of H_2O_2 (30%)) was added to oxidize the organic carbonates to CO_2 . The released CO_2 was again quantified by a MS. electrochemical oxidation by linear sweep voltammetry (LSV) with a voltage cutoff of 4.2 V. The electrolyte was extracted from all cell components using DMSO- d_6 for further experiment. ^1H -NMR spectra were recorded on a Bruker Avance III 300MHz FT NMR spectrometer with autosampler (300.36MHz, DMSO- d_6). We lack an effective way to quantify the $^1\text{O}_2$ during charging to such a high potential of 4.7 V. On one hand, DMA decomposes above 4.2 V and thus we cannot

use DMA to detect $^1\text{O}_2$ at 4.7 V. However, there is only a small portion (<5%) of Li_2CO_3 decomposes below 4.2 V and the amount of $^1\text{O}_2$ at this stage is low, which could not represent the overall reaction up to 4.7 V. For the aspect of energy, more $^1\text{O}_2$ would format a higher potential. On the other hand, the NMR is only a semi-quantitative technique. Thus probing DMA- O_2 using NMR could only confirm the formation of $^1\text{O}_2$ but it could not provide a reliable quantification of such a low amount of $^1\text{O}_2$. The NMR of the electrolyte in a cell with Co_3O_4 is shown in Supplementary Fig. 18. The cell was charged by LSV to 4.2 V. The electrolyte was extracted from all cell components using DMSO-d_6 . The signals of DMA O_2 in both samples are too weak to compare quantitatively.

Chemical experiments between reactive oxygen species and carbon

The purpose of this ex situ chemical experiment is to identify the products of reactive oxygen species attacking ^{13}C -carbon. We try to prove the feasibility that $^1\text{O}_2$ attacks ^{13}C -carbon to form $^{13}\text{CO}_2$ and ^{13}CO , which is detected during the charging process of the cell with Li_2CO_3 . Meanwhile, our results show that superoxide species could not oxidize ^{13}C -carbon to form $^{13}\text{CO}_2$ and ^{13}CO .

Singlet oxygen was obtained by the disproportionation of superoxide species, which is KO_2 and Li^+ here. Briefly, a varying amount of ^{13}C -carbon and 22mg KO_2 powder was added to a vial that is connected to a MS before the solution is added into the vial. The carrier gas will be passed for a period to eliminate the residual gas in the vial. Then, 1mL high concentration lithium salt electrolyte (4M LiTFSI here) was injected into the vial to react with KO_2 to disproportionate to produce $^1\text{O}_2$. $^1\text{O}_2$ immediately oxidized ^{13}C -carbon to evolve $^{13}\text{CO}_2$ and ^{13}CO . The produced gases were detected by a MS. An excess amount of KO_2 was used here to produce a large amount of $^1\text{O}_2$. So far, we could not quantify the amount of $^1\text{O}_2$ produced in this disproportionation reaction of KO_2 and Li^+ . Here, the experiments were carried out without applying a potential, namely at "OCV". The reactivity of carbon and the ratio of CO_2/CO may change when voltage is applied. The impact of potential in the side-reaction of $^1\text{O}_2$ and ^{13}C is not the focus of this work. Also, when a high potential is applied to the carbon substrate, electrode decomposition will take place, which makes the situation complicated to decouple these factors. Here, we mainly focus on Li_2CO_3 electro-oxidation. Although carbon oxidation accompanies Li_2CO_3 decomposition, it only contributes to ~10% of the total CO_2 evolution.

A control experiment of superoxide attacking ^{13}C -carbon was carried out to make a comparison. Superoxide was obtained as previously reported⁵². In brief, firstly, argon was used to exclude the dissolved gas such as oxygen in the tetraglyme solvent. Then, 71mg KO_2 and 264mg 18-crown-6 were added to 10mL tetraglyme electrolyte and stirred for four hours to maximize the concentration of the O_2 (sol). The electrolyte was centrifuged and the supernatant also was injected with argon to get out the dissolved oxygen produced by the KO_2 attack electrolyte for further experiment. Finally, varying amounts of ^{13}C -carbon powder were added to a vial and 1 mL supernatant was injected into the vial for the source of superoxide. The produced gases were detected by a MS.

In the charging process of the cell, because Li_2CO_3 has ultralow ionic and electronic conductivities, its decomposition takes place at the $^{13}\text{C}|\text{Li}_2\text{CO}_3$ solid-solid interface (namely the contact points between ^{13}C

particles and Li_2CO_3 particles). Therefore, the decomposition product, $^1\text{O}_2$, is just formed at this interface, which is very close to ^{13}C , and thus it is easy to attack ^{13}C . Therefore, the ratio between $^1\text{O}_2$ and ^{13}C is high. On the contrary, in the chemical experiments described above, $^1\text{O}_2$ originates from the disproportionation of superoxide in the solution phase. Although ^{13}C was added to the solution and stirring was applied, the fresh $^1\text{O}_2$ forms from the disproportionation process in the electrolyte and it first attacks the electrolyte. Only a small portion of $^1\text{O}_2$ would diffuse to the surface of the suspended ^{13}C in the electrolyte and react with ^{13}C . In addition, the ratio of releasing $^1\text{O}_2$ from disproportionation is still unknown, which is highly likely below 10%. Freunberger et al show that more $^1\text{O}_2$ forms during the charging process than in the discharging process involving disproportionation.

Quenching $^1\text{O}_2$

Once the $^1\text{O}_2$ forms in the electrolyte, it is too late to stabilize it and it rapidly attacks the electrolyte and carbon substrate. Therefore, our strategy is to stabilize this intermediate/precursor which further produces singlet oxygen, rather than to quench the $^1\text{O}_2$ after its formation in the electrolyte. In this case, we hope that Co_3O_4 binds the intermediate (namely the precursor of $^1\text{O}_2$, e.g. CO_4^{2-}) into a complex such as $\text{Co}_3\text{O}_4\text{-CO}_4$, before $^1\text{O}_2$ is formed and dissolved in the electrolyte. Our experimental results show that Co_3O_4 makes some positive effects, but it is not good enough. If it works properly, the ratio(CO_2/O_2) should be 2 according to the equ 1a, but the ratio(CO_2/O_2) Co_3O_4 is 6.7, much higher than 2. It might be a feasible strategy to inhibit $^1\text{O}_2$ formation but there are still lots of work that need to be done.

Acknowledgements

I am very much grateful to Prof. Rabindra Singh, HOD, Dept. of Chemistry, J.P. University, Chapra, Prof. Udai Arvind, Dean Science, J.P. University, Chapra, Prof. U.S. Yadav, former HOD, Deptt. Of Chemistry, J.P. University, Chapra, Dr. Sanjay Kr., Associate Prof. Deptt. Of Chemistry, Jagdam College, Chapra for their innovative and valuable suggestions and moral support for the same.

References

1. Kwak, W. J. et al. Lithium-oxygen batteries and related systems: potential, status, and future. *Chem. Rev.* 120, 6626–6683 (2020).
2. Liu, T. et al. Current challenges and routes forward for nonaqueous lithium-air batteries. *Chem. Rev.* 120, 6558–6625 (2020).
3. Zhao, Z. et al. Achilles' heel of lithium-air batteries: lithium carbonate. *Angew. Chem. Int. Ed. Engl.* 57, 3874–3886 (2018).
4. Leverick, G. et al. Solvent and anion dependent $\text{Li}^+\text{-O}_2^-$ coupling strength and implications on the thermodynamics and kinetics of Li- O_2 batteries. *J. Phys. Chem. C.* 124, 4953–4967 (2020).

5. Feng, N. et al. Critical challenges in rechargeable aprotic Li-O₂ batteries. *Adv. Energy Mater.* 6, 1–24 (2016).
6. Abraham, K. M. & Jiang, Z. A polymer electrolyte-based rechargeable. *J. Electrochem. Soc.* 143, 1–5 (1996).
7. Ko, Y. et al. Anchored mediator enabling shuttle-free redox mediation in lithium-oxygen batteries. *Angew. Chem. Int. Ed. Engl.* 59, 5376–5380 (2020).
8. Xu, S. M. et al. Surface engineering donor and acceptor sites with enhanced charge transport for low-overpotential lithium-oxygen batteries. *Energy Stor. Mater.* 25, 52–61 (2020).
9. OttakamThotiyil, M. M. et al. The carbon electrode in nonaqueous Li- O₂ cells. *J. Am. Chem. Soc.* 135, 494–500 (2013).
10. Kwak, W. J. et al. Effects of fluorinated diluents in localized highconcentration electrolytes for lithium-oxygen batteries. *Adv. Funct. Mater.* 31, 2002927 (2021).
11. Yin, W. et al. Chemical vs electrochemical formation of Li₂CO₃ as a discharge product in Li-O₂/CO₂ batteries by controlling the superoxide intermediate. *J. Phys. Chem. Lett.* 8, 214–222 (2017).
12. Gowda, S. R. et al. Implications of CO₂ contamination in rechargeable nonaqueous Li-O₂ batteries. *J. Phys. Chem. Lett.* 4, 276–279 (2013).
13. Lim, H. K. et al. Toward a lithium-air battery: the effect of CO₂ on the chemistry of a lithium-oxygen cell. *J. Am. Chem. Soc.* 135, 8733–9742 (2013).
14. Bruce, P.G. et al. Li-O₂ and Li-S batteries with high energy storage. *Nat. Mater.* 11, 19–29 (2013).
15. Aurbach, D. et al. Advances in understanding mechanisms underpinning lithium-air batteries. *Nat. Energy* 1, 16128 (2016).
16. Mu, X., Pan, H., He, P. & Zhou, H. Li-CO₂ and Na-CO₂ batteries: toward greener and sustainable electrical energy storage. *Adv. Mater.* 32, 1903790 (2020).
17. Liu, B. et al. Recent advances in understanding Li-CO₂ electrochemistry. *Energy Environ. Sci.* 12, 887–922 (2019).
18. Bie, S. et al. Carbon nanotube@RuO₂ as a high performance catalyst for Li-CO₂ batteries. *ACS Appl. Mater. Inter.* 11, 5146 5151 (2019).
19. Liu, Y., Wang, R., Lyu, Y., Li, H. & Chen, L. Rechargeable Li/CO₂-O₂ (2:1) battery and Li/CO₂ battery. *Energy Environ. Sci.* 7, 677–681 (2014).
20. Zhang, Z. et al. The first introduction of graphene to rechargeable Li-CO₂ batteries. *Angew. Chem. Int. Ed. Engl.* 54, 6550–6553 (2015).
21. Qie, L., Lin, Y., Connell, J. W., Xu, J. & Dai, L. Highly rechargeable lithium-CO₂ batteries with a boron- and nitrogen-codoped holeygraphene cathode. *Angew. Chem. Ed. Engl.* 56, 6970–6974 (2017).
22. Zhang, X. et al. Rechargeable Li-CO₂ batteries with carbon nanotubes as air cathodes. *ChemComm* 51, 14636–14639 (2015).

23. Hou, Y. et al. Mo₂C/CNT: an efficient catalyst for rechargeable Li- CO₂ batteries. *Adv. Funct. Mater.* 27, 1700564 (2017).
24. Li, S. et al. Monodispersed MnO nanoparticles in graphene-an interconnected N-doped 3D carbon framework as a highly efficient gas cathode in Li-CO₂ batteries. *Energy Environ. Sci.* 12, 1046–1054 (2019).
25. Zhang, X. et al. High performance Li-CO₂ batteries with NiO-CNT cathodes. *J. Mater. Chem. A.* 6, 2792–2796 (2018).
26. Xu, S., Das, S. K. & Archer, L.A. The Li-CO₂ battery: a novel method for CO₂ capture and utilization. *RSC Adv.* 3, 6656 (2013).
27. Qiao, Y. et al. Li-CO₂ electrochemistry: a new strategy for CO₂ fixation and energy storage. *Joule* 1, 359–370 (2017).
28. Yang, S., He, P. & Zhou, H. Exploring the electrochemical reaction mechanism of carbonate oxidation in Li-air/CO₂ battery through tracing missing oxygen. *Energy Environ. Sci.* 9, 1650–1654 (2016).
29. Zhang, B.W. et al. Targeted synergy between adjacent Co atoms on graphene oxide as an efficient new electrocatalyst for Li-CO₂ batteries. *Adv. Funct. Mater.* 29, 1904206 (2019).
30. Cai, F. S., Hu, Z. & Chou, S. L. Progress and future perspectives on Li(Na)-CO₂ batteries. *Adv. Sustain. Syst.* 2, 1800060 (2018).
31. Cui, C. Y. et al. Structure and interface design enable stable Li-rich cathode. *J. Am. Chem. Soc.* 142, 8918–8927 (2020).
32. Liu, J. et al. Recent breakthroughs and perspectives of high-energy layered oxide cathode materials for lithium ion batteries. *Mater. Today* 43, 132–165 (2021).
33. Kaufman, L. A. & McCloskey, B. D. Surface lithium carbonate influences electrolyte degradation via reactive oxygen attack in lithium-excess cathode materials. *Chem. Mater.* 33, 4170–4176 (2021).
34. Renfrew, S. E. & McCloskey, B. D. Residual lithium carbonate predominantly accounts for first cycle CO₂ and CO outgassing of Li-stoichiometric and Li-rich layered transition-metal oxides. *J. Am. Chem. Soc.* 139, 17853–17860 (2017).
35. Renfrew, S. E. & McCloskey, B. D. Quantification of surface oxygen depletion and solid carbonate evolution on the first cycle of LiNi_{0.6}Mn_{0.2}Co_{0.2}O₂ electrodes. *ACS Appl. Energy Mater.* 2, 3762–3772 (2019).
36. Wang, H. et al. CO₂ and O₂ evolution at high voltage cathode materials of Li-Ion batteries: a differential electrochemical mass spectrometry study. *Anal. Chem.* 86, 6197–6201 (2014).
37. Hatsukade, T., Schiele, A., Hartmann, P., Brezesinski, T. & Janek, J. Origin of carbon dioxide evolved during cycling of nickel-rich layered NCM cathodes. *ACS Appl. Mater. Inter.* 10, 38892–38899 (2018).
38. Cheng, L. et al. The origin of high electrolyte-electrode interfacial resistances in lithium cells containing garnet type solid electrolytes. *Phys. Chem. Chem. Phys.* 16, 18294–18300 (2014).

39. Cheng, L. et al. Interrelationships among grain size, surface composition, air stability, and interfacial resistance of Al-substituted $\text{Li}_7\text{La}_3\text{Zr}_2\text{O}_{12}$ solid electrolytes. *ACS Appl. Mater. Inter.* 7, 17649–17655 (2015).
40. Bi, Y. et al. Stability of Li_2CO_3 in cathode of lithium ion battery and its influence on electrochemical performance. *RSC Adv.* 6, 19233–19237 (2016).
41. Freiberg, A. T. S., Sicklinger, J., Solchenbach, S. & Gasteiger, H. A. Li_2CO_3 decomposition in Li-ion batteries induced by the electrochemical oxidation of the electrolyte and of electrolyte impurities. *Electrochim. Acta* 346, 136271 (2020).
42. Wandt, J., Freiberg, A. T. S., Ogrodnik, A. & Gasteiger, H. A. Singlet oxygen evolution from layered transition metal oxide cathode materials and its implications for lithium-ion batteries. *Mater. Today* 21, 825–833 (2018).
43. Freiberg, A. T. S., Roos, M. K., Wandt, J., de Vivie-Riedle, R. & Gasteiger, H. A. Singlet oxygen reactivity with carbonate solvents used for Li-Ion battery electrolytes. *J. Phys. Chem. A* 122, 8828–8839 (2018).
44. Ling, C. et al. Intrinsic barrier to electrochemically decompose Li_2CO_3 and LiOH . *J. Phys. Chem. C* 118, 26591–26598 (2014).
45. Garcia-Lastra, J. M. et al. DFT +U study of polaronic conduction in Li_2O_2 and Li_2CO_3 . Implications for Li-Air batteries. *J. Phys. Chem. C* 117, 5568–5577 (2013).
46. Mahne, N., Renfrew, S. E., McCloskey, B. D. & Freunberger, S. A. Electrochemical oxidation of lithium carbonate generates singlet oxygen. *Angew. Chem. Int. Ed. Engl.* 57, 5529–5533 (2018).
47. Wang, Y., Alsmeyer, D. C. & McCreery, R. L. Raman spectroscopy of carbon materials: structural basis of observed spectra. *Chem. Mater.* 2, 557–563 (1990).
48. Mahne, N. et al. Singlet oxygen generation as a major cause for parasitic reactions during cycling of aprotic lithium-oxygen batteries. *Nat. Energy* 2, 17036 (2017).
49. Chaisiwamongkhol, K. et al. Singlet oxygen and the origin of oxygen functionalities on the surface of carbon electrodes. *Angew. Chem. Ed. Engl.* 130, 6378–6381 (2018).
50. Kwak, W. J. et al. Deactivation of redox mediators in lithium-oxygen batteries by singlet oxygen. *Nat. Commun.* 10, 1380 (2019).
51. Freunberger, S. A. et al. Reactions in the rechargeable lithium- O_2 battery with alkyl carbonate electrolytes. *J. Am. Chem. Soc.* 133, 8040–8047 (2011).
52. Petit, Y. K. et al. Mechanism of mediated alkali peroxide oxidation and triplet versus singlet oxygen formation. *Nat. Chem.* 13, 465–471 (2021).
53. Hiroshi, Y. et al. Method of purifying lithium hexafluorophosphate. US, US6884403 B2. (2001).
54. Jiang, F. et al. Deciphering the enigma of Li_2CO_3 oxidation using a solid-state Li-Air battery configuration. *ACS Appl. Mater. Inter.* 13, 14321–14326 (2021).

55. Gao, X., Chen, Y., Johnson, L. & Bruce, P. G. Promoting solution phase discharge in Li-O₂ batteries containing weakly solvating electrolyte solutions. *Nat. Mater.* 15, 882–888 (2016).
56. Lin, Y. et al. Suppressing singlet oxygen formation during the charge process of Li-O₂ batteries with a Co₃O₄ solid catalyst revealed by operando electron paramagnetic resonance. *J. Phys. Chem. Lett.* 12, 10346–10352 (2021).
57. OttakamThotiyil, M. M., Freunberger, S. A., Peng, Z. Q. & Bruce, P.G. The carbon electrode in nonaqueous Li-O₂ cells. *J. Am. Chem. Soc.* 135, 494–500 (2013).

