



# Analysis Of Design and Material Selection of a Spur Gear for Industrial Application

**Dr. P. Nagasankar, S. Aripasath, V. Kishore, Ajay B Krishna.,**

Professor, Student, Student, Student, Mechanical Engineering.  
Vel Tech High Tech Dr. Rangarajan Dr. Sakunthala Engineering College. Chennai, India.

**Abstract:** Aluminum alloys have extensive application in industries. The range of physical properties that can be imparted to them is remarkable. Addition of Silicon to Aluminum helps to increase their strength and wear resistance. Al-Si alloys are extensively used in industrial applications due to better tribological properties. In the present work, an attempt has been made to study the tribological properties of two Aluminum as-cast alloy samples i.e., Al-7wt%Si, Al-10wt%Si. Wear tests were conducted using a pin-on-disc type wear testing machine (DUCOM wear and friction monitor) after metallographic examination followed by hardness measurement. The operational parameters that were varied were percentage of Silicon content of the alloy, normal load, sliding velocity, sliding distance and lubrication. The wear was higher at increased velocity at increased normal load. Wear was found to be increasing with decreasing Silicon content. SEM characterization was done. Interestingly, wear under lubricated condition was higher. The interaction of Silicon platelets at the Al-Si boundary might have been the possible reason. Spur Gear is to be designed and modeled in CATIA and simulate in ANSYS.

## 1.INTRODUCTION

### 1.1 BACKGROUND

Aluminum (Al) is the second-most plentiful element on earth and it became an economic competitor in the engineering applications as early as the end of the 19<sup>th</sup> century. The emergence of three important industrial revolutions would, by demanding material characteristics consistent with the unique qualities of Aluminum and its alloys, greatly benefit growth in the production and use of the metal.

Among the most striking characteristics is its versatility. The range of physical properties that can be developed-from refined high-purity Al to the most complex alloys-is remarkable.

Aluminum and its alloys are extensively used as the materials in transportation (aerospace and automobiles), engine components and structural applications. Thus, it becomes all the more vital to study the tribological characteristics of Aluminum and its alloys. Addition of Silicon to Aluminum gives high strength to weight ratio, low thermal expansion coefficient, and high wear resistance. These alloys also show improved strength and wear properties as the silicon content is increased beyond eutectic composition. Such properties warrant the use of these materials as structural components in automotive industries. The wear properties of three Aluminum alloy samples have been studied viz. Al-7wt% Si, Al-10%Si and Al-14%Si here. The principal wear mechanisms in these alloys and abrasive and sliding wear which have been dealt with in the later part of this work.

### 1.2 WHY ALUMINIUM ALLOYS

The properties of Aluminum and its alloys that make them the most economically attractive for a wide variety of applications are

- i. **Light weight:** Aluminum weighs roughly one-third as much as most of the common metals, but is one and a half times as heavy as Magnesium. It finds application to reduce weight of components and structures, particularly connected with transport, especially with aerospace.
- ii. **High Strength-to-weight ratio:** High Strength-to-weight ratio saves a lot commercially, when dead weight is decreased and payload of transport is increased. This ratio is of particular significance in engineering designs where stiffness is involved. For example, stiffness for equal weights of similar beams is in ratio 1:2.9:8.2:18.9 for steel, Titanium, Aluminum and Magnesium respectively.
- iii. **Ease of fabrication and machinability:** It can be easily cast, rolled to any desired thickness (aluminum foils are so common), stamped, drawn, spun, forged and extruded to all shapes.
- iv. **High resistance to atmospheric corrosion:** When aluminum is exposed to air, a thin oxidized film forms on the surface, protecting the metal from corrosion. When scratched, the layer rapidly reforms retaining the protection. This feature is utilized in construction, buildings and household utensils.
- v. **Resilience under static and dynamic loading:** Aluminum products behave elastically under static and dynamic loading conditions, that is, they have the ability to resume both shape and size which is good when flexible strength is required. Mast

and spars of racing yachts are designed to withstand the stress of the wind versus the waves. vi. **Strength at low temperature:** Brittle fracture problems do not occur with aluminum. As the temperature is reduced, aluminum alloys increase in strength without loss in quality, making them particularly suitable for low temperature applications.


### 1.3 Aluminum-Silicon Alloys:

#### 1.3.1 Aluminum-Silicon Eutectic and hypoeutectic alloys:

Alloys with Silicon as a major alloying element are by far the most important commercial casting alloys, primarily because of their superior casting characteristics in comparison to other alloys. A wide range of physical and mechanical properties is afforded by these alloys. Binary aluminum-silicon alloys combine the advantages of high corrosion resistance, good weldability, and low specific gravity. Although castings of these alloys are somewhat more difficult to machine than the aluminum-copper or aluminum-magnesium alloys, all types of machining operations are routinely accomplished, usually using Tungsten carbide tools and appropriate coolants and lubricants.

Alloy 443 (5.3% Si) may be used for all casting processes for parts in which good ductility, good corrosion resistance, and pressure tightness are more important than strength. For die casting, alloys 413 and A 413 (12% Si) also have good corrosion resistance but are superior to alloy 443 in terms of castability and pressure tightness. Alloy A444 (7% Si-0.2% iron, maximum) also has good corrosion resistance and has especially high ductility when cast in permanent mold and heat treated to a T4 condition. This alloy has good impact resistance.

Alloys 413, 443 and 444 are important binary aluminum-silicon alloys. Another group of aluminum-silicon alloys however represents the workhorse aluminum foundry alloys. In this group, silicon provides good casting characteristics and copper imparts moderately high strength and improved machinability, at the expense of somewhat reduced ductility and lower corrosion resistance. Alloy 319 (6% Si-3.5% copper) is a preferred general-purpose alloy for sand foundries that may also be used in permanent mold casting.

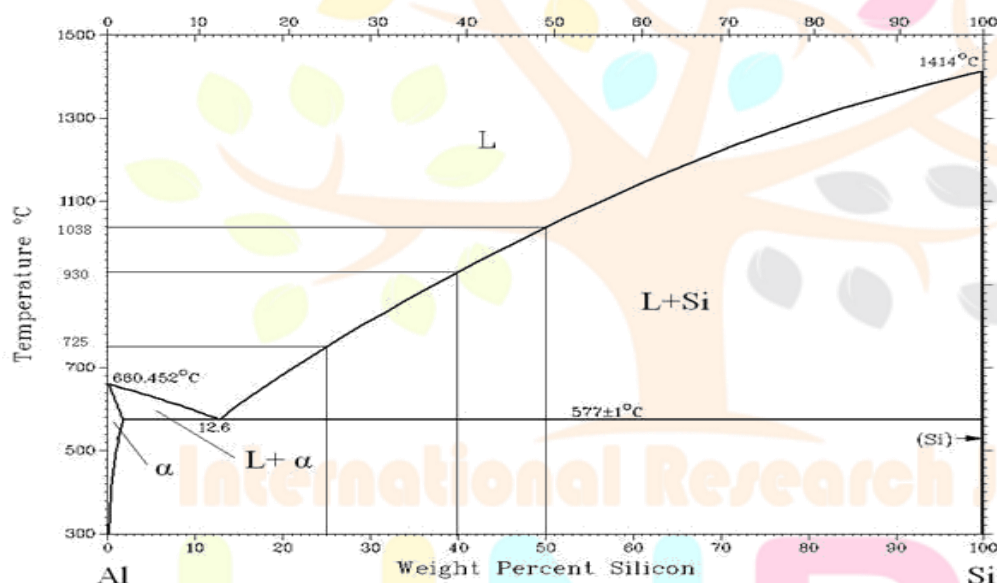

*Fig 1.1 The Aluminum Silicon binary phase diagram. The eutectic occurs at 12.6 wt% Si*

#### 1.3.2 Hypereutectic aluminum-silicon alloys:

Aluminum silicon alloys with greater than 12% Silicon are called hypereutectic aluminum-silicon alloys. These have outstanding wear resistance, a lower thermal expansion coefficient, and very good casting characteristics. Such alloys have limited use because the presence of the extremely hard primary Silicon phase reduces tool life during machining. Also, the special foundry characteristics and requirements of this alloy system, needed to properly control microstructure and casting soundness, are not clearly as well understood as are the characteristics of conventional hypoeutectic alloys.

These alloys have outstanding fluidity and excellent machinability in terms of surface finish and chip characteristics. A typical example is 390 alloy (17% silicon-4.5% copper-0.5% magnesium) whose outstanding wear characteristics have caused a rapid growth in its use. It is used in small engines, pistons for air conditioning compressors, master brake cylinders, and pumps and other components in automatic transmission.

### 1.4 Wear

It is defined as a process of removal of material from one or both of two solid surfaces in solid contact. Wear is defined as “the damage to a solid surface, generally involving the progressive loss of material, due to relative motion between two moving surfaces”. Such a process is complicated, involving time-dependent deformation, failure and removal of materials at the counter face. Research in this area is of vital importance from the economic point of view because it is a major problem and its direct cost is estimated to vary between 1% and 4 % of a nation’s Gross National Product.

### 1.4.1 Types of wear

Following are the various types of wear processes based on the types of wearing contacts.

1. **Single-phase wear:** In which a solid moving relative to a sliding surface causes material to be removed from the surface.  
The relative motion for wear to occur may be sliding or rolling.
2. **Multi-phase wear:** In which wear, from a solid, liquid or gas acts as a carrier for a second phase that actually produces the wear.

### 1.4.2 Wear Mechanisms

Common types of wear mechanisms are as listed below

- (i) Abrasive wear
- (ii) Solid particle erosion
- (iii) Sliding and adhesive wear
- (iv) Fretting wear
- (v) Corrosive wear
- (vi) Impact wear


#### ABRASIVE WEAR:

Abrasive wear occurs when a hard rough surface slides across a softer surface. ASTM (American Society for Testing and Materials) defines it as the loss of material due to hard particles or hard protuberances that are forced against and move along a solid surface.

Wear, in turn, is defined as damage to a solid surface that generally involves progressive loss of material and is due to relative motion between that surface and a contacting substance or substances. The rate at which the surfaces abrade depends on the characteristics of each surface, the presence of abrasives between the first and second surfaces, the speed of contact, and other environmental conditions. In short, loss rates are not inherent to a material.

#### MECHANISMS PROPOSED

Many mechanisms have been proposed to explain how material removal during abrasion. These mechanisms include fracture, fatigue, and melting. Due to the complexity of abrasion process, no single mechanism completely accounts for all the loss. Figure 1.2 depicts some of the processes which are possible when a single abrasive tip slides across a surface. They include plowing, wedge formation, cutting, micro fatigue, and microcracking.

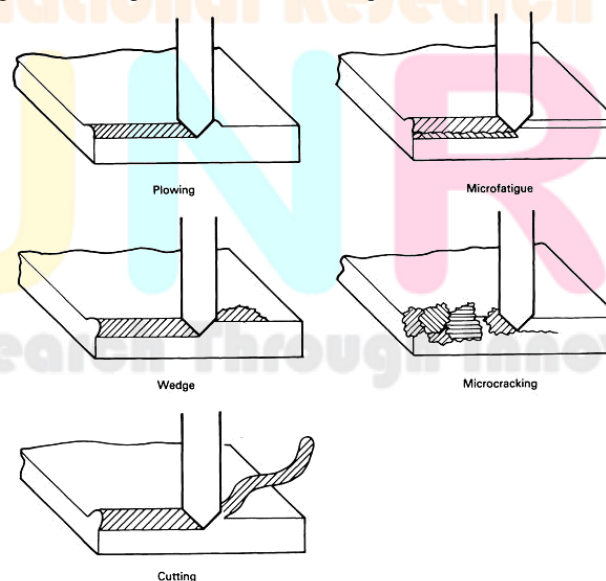

**Fig1.2. Five processes of abrasive wear • SOLID PARTICLE EROSION (SPE)**

It is the loss of material that results from repeated impact of small, solid particles. In some cases, SPE is a useful phenomenon, as in sandblasting and highspeed abrasive waterjet cutting, but it is a serious problem in many engineering systems, including steam and jet turbines, pipelines and valves carrying particulate matter, and fluidized bed combustion (FBC) systems. Solid particle erosion is to be expected whenever hard particles are entrained in a gas or liquid medium impinging on a solid at any significant velocity (greater than 1 m/s, or 3.3 ft/s). Manifestations of SPE in service usually include thinning of components, a macroscopic scooping appearance following the gas/particle flow field, surface roughening (ranging from



polishing to severe roughening, depending on particle size and velocity), lack of the directional grooving characteristic of abrasion, and, in some but not all cases, the formation of ripple patterns on metals.


Solid particle erosion can occur in a gaseous or liquid medium containing solid particles. In both cases, particles can be accelerated or decelerated, and their directions of motion can be changed by the fluid. This is more significant in liquid media, and slurry erosion is generally treated as a different, though related, subject. In gaseous media, at least for particles larger than about 50 m, deflection of the particles by the gas stream can often be ignored in erosion tests.

The distinction between erosion and abrasion should be clarified, because the term erosion has often been used in connection with situations that might be better classed as abrasion. Solid particle erosion refers to a series of particles striking and rebounding from the surface, while abrasion results from the sliding of abrasive particles across a surface under the action of an externally applied force. The clearest distinction is that, in erosion, the force exerted by the particles on the material is due to their deceleration, while in abrasion it is externally applied and approximately constant.

#### • **SLIDING AND ADHESIVE WEAR**

It is a type of wear generated by the sliding of one solid surface against another. Erosion, cavitation, rolling contact, abrasion, oxidative wear, fretting, and corrosion are traditionally excluded from the class of "sliding" wear problems even though some sliding may take place in some of these types of wear. Apparently, sliding wear is a type of wear that is "left over" when all other types of wear have been identified under separate headings.

Although sliding wear and adhesive wear are not synonymous, Adhesive wear is as ambiguously defined as sliding wear. This phenomenon denotes a wearing action in which no specific agency can be identified as the cause of wear. Adhesive wear is said to occur if no abrasive substances are found, amplitude of sliding is greater than that in fretting and oxidation does not take place.

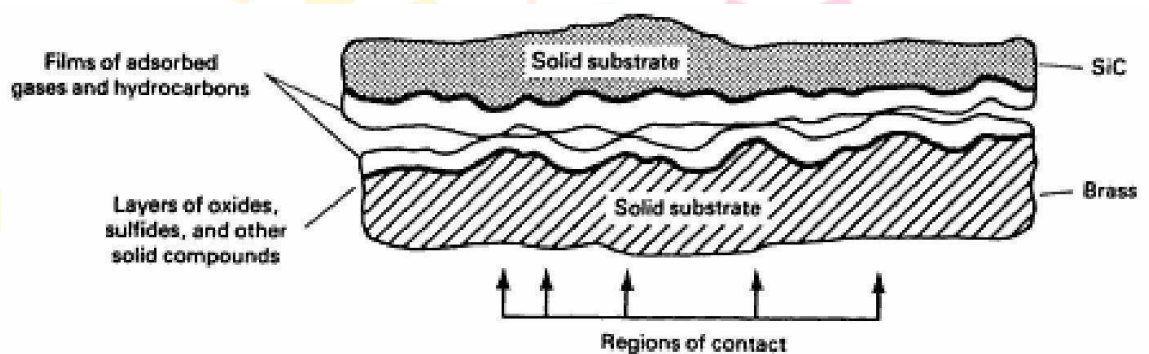

**Fig 1.3 Schematic of a bond bridge produced when two solid surfaces are in contact with each other. It should be noted that when two rough surfaces are brought together, actual contact occurs only in a few isolated regions**

#### **FRETTING WEAR**

Fretting can be defined as the "small-amplitude oscillatory movement that may occur between contacting surfaces, which are usually nominally at rest." Production of oxide debris is one of the immediate consequences of this phenomenon. Hence, the terms "fretting wear" and "fretting corrosion" are applied to this process. The movement is due to external vibration. But in several cases, one of the members of the contact is subjected to a cyclic stress (fatigue). This gives rise to the initiation of fatigue cracks. This is called "fretting fatigue" or "contact fatigue"

#### **CORROSIVE WEAR**

In case of corrosive wear, thin films are assumed to form through rotochemical reactions between contact surface materials and surrounding media, such as air or a liquid lubricant and wear occurs through a combination of wear and corrosion can result in total material losses that are much greater than the additive effects of each process taken alone, which shows synergism between the two processes. Corrosion accompanies the wear process to some extent in all environments, except in inert atmospheres

#### **IMPACT WEAR**

It is defined as wear of a solid surface due to percussion. Percussion is a repetitive exposure to dynamic contact by another solid body. Several industries employ processes that lead to impact wear. Machine components, cams, and gears mate with a certain dynamic component. Typical applications occur in electromechanical printers; a prime example is that of typefaces, which are expected to hold definition, thus assuring high print quality, often for billions of cycles.

## LITERATURE SURVEY

The literature survey is carried out to study and evaluate the wear properties of Al-Si alloys. The various parameters such as Silicon content, applied load, sliding distance, effect of microstructure, etc. have been studied. The work of researchers in this respect is been considered. Their conclusions are as follows:

Haydar Al-Ethari, Ali Hubi Haleem and Muhanad Hamidhassan., **“Investigation on Wear Behavior of Al-Si Eutectic Alloy.”** (2021) Samples of aluminum-silicon eutectic alloys were cast via stir casting method to investigate their wear behavior. Three types of samples were prepared. The first solidified under the effect of mechanical vibration (using an amplitude of 0.5 mm and a frequency of 25 Hz); the second has an addition of 0.13 wt% titanium as alloying element; while the third cast with the combined effect of added titanium and mold vibration. Chemical composition test, scanning electron microscope (SEM) analysis, macro-hardness and wear tests were done for the prepared samples. The results showed that at 27 °C for 25-minute loading with a load of 20 N, the lowest wear rate of sample prepared with the combined effect of mold vibration and addition of titanium, the biggest wear rate for sample with the effect of vibration, and the wear rate of sample prepared with addition of titanium between them. The wear rate at 100 °C is lesser than that at 27 °C for all samples at the same conditions.

H. Turabian, J. B Pathak and S.N. Tiwari., **“The Dry Sliding Wear Behavior of Aluminum Composites** (2019) have studied the effects of alloy composition, sliding distance, sliding speed and load on the wear rate of Al-Si alloys.

The wear rate is strongly dependent on the applied load. It increases linearly with load in three distinct regions in all the alloys. Mild wear, Intermediate wear and Severe wear. Mild wear takes a longer duration and takes place under low loads. The intermediate wear and severe wear regions are distinguished from the mild region by higher rates of increase in the wear rate per unit weight.

It may be observed that the transition load at which change takes place from one region to other increases with increased Silicon content of the alloy. It is observed that wear rate initially decreases slightly with increasing sliding speed up to a certain value. Beyond this, there is a sharp rise in the wear rate, irrespective of the alloy composition. This value increases with increasing Silicon content.

The wear rate of the alloy is strongly dependent on the Silicon content of the alloy. The wear rate is found to decrease with increasing Silicon content. This effect is pronounced up to 15% Si in the alloy. Thus, wear rates of hypereutectic alloys are better than those of hypoeutectic alloys.

D. Odaiba's., **“The Influence of The Temperature on Dry Friction of AISi 3315 Steel Sliding Against AISI 3150 Steel”** (2018) worked on the comparison of reciprocating and continuous two body abrasive wear behavior of solution-treated and age-hardened 2014 Al alloy. Reciprocating and continuous abrasive wear have been performed on solution treated 2014 Al alloys under similar conditions of load, speed, nominal area of contact and sliding distance. In order to compare the two-body abrasive wear behavior for two sliding modes. Pattern of wear is similar for both. But the average roughness in continuous wear is more than that of reciprocating. Because wear loss and abrasive wear coefficient in continuous wear is higher than that of reciprocating Sliding distance differences can explain this phenomenon  
Conclusions can be drawn as-

Difference in continuous and reciprocating wear

Wear loss is greater in the continuous wear.

The abrasive wear coefficient is higher in the continuous wear.

The above phenomenon is explained by difference in sliding distance in both the cases and the greater amount of abrasion of the loose wear debris trapped between the contact surface of the pin and abrasive paper for much longer in the continuous wear mode.

Latina Hu, Jianmin Chun, Weimin Liu, Qunji Xue and Czeslaw Kajdas., **“Investigation of Tribiochemical Behavior of Al-Si Alloy Against Itself Lubricated by Amines.”** (2017) have studied the wear and friction properties of Al-Si alloy against itself with the lubrication of pure ethylene glycol, ethanolamine, ethylenediamine and triethylenetetramine.

Friction and wear tests showed that the friction coefficient for triethylenetetramine was lowest. Wear of the Al-Si alloy lubricated with ethylene glycol was the largest whereas triethylenetetramine produced the best results. This has been explained on a molecular level. In amine like compounds, there are two electrons in the Nitrogen atom which are not bonded. Thus, it is easy to interact with metals. In triethylenetetramine, though Nitrogen percentage is smaller than that in diamines, it exhibits better tribological behavior. As sliding goes on, these loosened particles are thrown away showing higher loss in weight. Heat treated alloys are not much affected due to their inherent characteristics due to heat treatment cycles whereas as cast alloys show higher weight loss. This has been explained by the fact that triethylenetetramine has a longer molecular chain. It also oxidizes easily and the oxidation products interact with the Al-Si alloy. Oxidation products may include  $\text{H}_2\text{NCH}_2\text{COOH}$  and  $\text{NHCH}_2\text{CH}_2\text{NH}_2$ . These products interact with the surface of the Al-Si alloy generated during sliding. It may also form some kind of a friction polymer.

Tutti Y. Alias and M.M Haque., **“Wear Properties of Aluminum Silicon Eutectic Alloy.”** (2017) have studied the wear behavior of as-cast and heat-treated Al-Si eutectic alloys. Wear tests on the alloys were performed on a pin on disk type wear testing apparatus and parameters were size and shape of the pin, load, speed and the material pairs.

Increase in the rotational speed of the disk leads to the increase in the mass loss of the as - cast and heat-treated alloys. The wear rate is higher for as -cast samples. High speed leads to reduction in wear rate. The reduction is pronounced in heat treated samples. This is because during sliding, heat is developed and the material becomes softer and weaker. This heat might not affect the hardness of heat-treated alloys due to their inherent characteristics.

Increase in the applied load leads to a high wear rate for both as-cast and heat-treated alloys. But at higher loads, strainhardening of the materials in contact increases, resulting in increase in the resistance to abrade or erode. At higher load, real surface area in contact is more which increases the gripping action and due to which wear rate slows down.

At longer sliding distances, volumetric wear rate and specific wear rate are low. This was attributed to the fact that during sliding, heat develops due to friction which makes some of the adhered materials soften and loosen. As sliding goes on, these loosened particles are thrown away showing higher loss in weight. Heat treated alloys are not much affected due to their inherent characteristics due to heat treatment cycles whereas as cast alloys show higher weight loss.

S.A. Kori and T.M. Chandrasekhara., **“Effect of Grain Refinement and Modification on The Dry Sliding Wear Behavior of Eutectic Al-Si Alloys.** (2016) have studied the effect of grain refiner and or modifier on the wear behavior of hypoeutectic (Al-0.2, 2, 3, 4, 5 and 7Si) and eutectic (Al- 12Si) alloys using a Pin-On-Disc machine under dry sliding conditions. It is important that Al-Si alloys solidify with fine equiaxed  $\alpha$ -Al in hypoeutectic/fine primary Si particles in hypereutectic and fine eutectic Si. This is because an oxide film is formed at high temperature which helps to avoid direct contact between alloy and the abrasive. Continuous sliding action removes this layer which facilitates direct contact of the alloy with the abrasive which results in decrement of wear rate at high temperature ( $\sim 300^\circ\text{C}$ ). While the former can be achieved by a suitable grain refinement treatment/solidification processing the later can be achieved by a suitable grain modification. A fine grain size ensures good tribological properties. Al-It-B was used as grain refiner and Al-10%Sr was used as modifier.

Addition of grain refiner and modifier to Al-Si alloys resulted in less specific wear rate for these samples. An increase in sliding speed led to the decrease of specific wear rate both in the case of grain refined/modified and grain unrefined/unmodified alloys. This may be due to the fact that, at low sliding speeds, more time is available for the formation and growth of micro welds, which leads to increase in the force required to shear off the micro welds to maintain the relative motion, resulting in an increase in specific wear rate. Less specific wear rate was observed in grain refined/modified alloys under these conditions.

Addition of grain refiner and modifier led to decrease in wear rate at longer sliding distances. Grain refinement and modification led to increase in toughness and strength of the alloy. Increase in Silicon content leads to solid solution strengthening and precipitation hardening and a subsequent increase in the strength of the alloy. Addition of grain refiner and modifier leads to better mechanical properties.

G. Rajaram, S. Kumaran and T. Srinivas Rao., **“Studies on High Temperature and Mechanism of Al-Si/Graphite Composite Under Dry Sliding Conditions”** (2017) have studied the tensile and wear properties of AlSi alloys fabricated by stircasting technique at temperatures ranging from ambient to  $350^\circ\text{C}$ . It is observed that the wear rate decreases with increasing temperature. This is because an oxide film is formed at high temperature which helps to avoid direct contact between alloy and the abrasive. Continuous sliding action removes this layer which facilitates direct contact of the alloy with the abrasive which results in decrement of wear rate at high temperature ( $\sim 300^\circ\text{C}$ ).

Another mechanism for this phenomenon has been suggested. At elevated temperatures, the agglomerated clusters of oxide formed due to tearing of oxide layers are subjected to thermal stresses and compaction by applied pressure and high temperature. Addition of Ce resulted in the formation of intermetallic phases like Al-Ce and Al-Si-Ce which leads to hardness and wear resistance. The volume loss of the alloys increased with increasing load and sliding distance. With increase in Ce content, volume loss decreased. This was due to the strong bonding between intermetallic phases and the matrix at the same time sintering of the wear debris is also occurring resulting in solid smooth hard surfaces called “glazes”. These glaze layers protect the sliding surface and reduce the wear rate.

Dhirendra Kumar Dwivedi., **“Studies on Machining Characteristics of Cast Al-Si Alloys.** (2021) has studied the effect of alloying elements on binary Al-17wt%Si alloy and multi-component (Al-17Si-0.8Ni-0.6Mg-1.2Cu-0.6Fe) cast alloy. A reduction in wear rate at high sliding speed was observed. This is due to the formation of an oxide layer on the sliding interface. Increase in the sliding speed leads to an increase in interface temperature. Rise in temperature increases the ability of soft Aluminum matrix to accommodate the hard and brittle Silicon. If temperature exceeds a certain critical value, thermal softening in the sub-surface region takes place which leads to large-scale plastic deformation.

Multi component alloys show better wear resistance because of increased solid solution strengthening, precipitation hardening and formation of intermetallic compounds in the presence of alloying elements. Formation of thermally stable intermetallic compounds and dispersion strengthening increase the wear resistance of multicomponent alloys. High hardness of these alloys is responsible for the low coefficient of friction during sliding due to easy fracture and deformation of asperities.

A.S Anasayida, A.R Daud and M.J Ghazali., **“Tribological Study of Aluminum Alloys.** (2019) have studied the effect of addition of Cerium on the wear behavior of as cast Al-4Si-4Mg alloys. Wear test results confirm that the wear rate decreases with the addition of Cerium in the alloy. The microstructures of the alloy samples reveal that Si in the as cast alloys is finely distributed in the interdimeric region. Silicon being harder than Aluminum increases the wear resistance of the alloys. Addition of Ce resulted in the formation of intermetallic phases like Al-Ce and Al-Si-Ce which leads to hardness and wear resistance. The volume loss of the alloys increased with increasing load and sliding distance. With increase in Ce content, volume loss decreased. This was due to the strong bonding between intermetallic phases and the matrix. Wear mechanisms involved were oxidative wear, micro cutting and delamination wear as shown by presence of oxides, microchips and delamination flakes. Cerium content up to 5% increased wear resistance.

#### 4.EXPERIMENTAL ANALYSIS

Casting of the Al-Si alloys were done by pouring the molten alloy into a copper mold of dimension  $1'' \times 2'' \times 3''$ . Grain modification was achieved by using sodium chloride. Cylindrical samples of diameter 10 mm each were machined from the ascast Al-Si alloys. Test samples are prepared from these cast ingots after polishing. The microstructure of the samples is observed under an optical microscope, after etched with Keller's reagent.



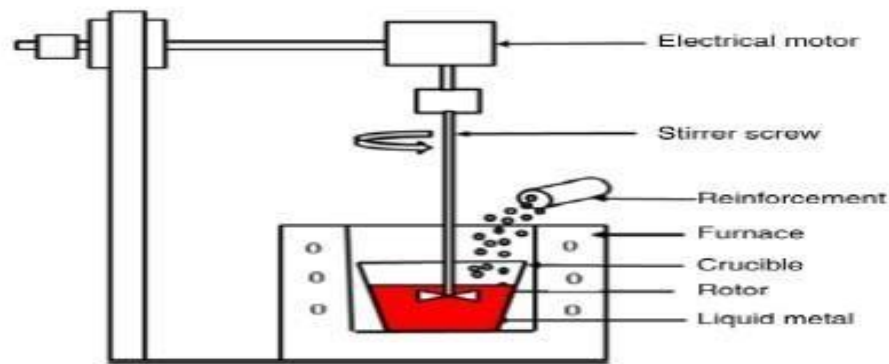


Fig4.1 Stir casting setup



Fig 4.2 Stir casting

#### 4.1 Hardness test:

The hardness values of these samples were determined by using Vickers's Micro hardness Tester with an applied load of 3 kgf.

#### 4.2 Wear tests:

##### 4.2.1 Abrasive wear test apparatus:

Test up used in the study of wear test is capable of creating reproducible abrasive wear situation accessing the abrasive wear resistance of the prepared samples. It consists of a pin on disc, loading panel and controller.



Fig4.3 DUCOM Wear and Friction Monitor used for the wear tests

All the test were carried out using a “Ducom friction and wear monitor” machine with both normal and lubricated condition. The normal condition has 50-60% relative humidity and a temperature of 28-32: C. The mass loss of the specimen after each test was estimated by measuring the height loss of the specimen due course of the experiment. The mass loss would be the height loss multiplied by the area of cross section of the sample and the density of the sample. Care has been taken to clean up the sample before and after each test to prevent any form of corrosion on the surface. Abrasive paper of required grit size (220  $\mu\text{m}$  optimized for the Al-Si sample) is cut into circular shape so as to fit in the ground steel disc and pasted on it with a proper adhesive ensuring no slide or detachment. The specimen was held steady and stationary with a holder of the apparatus and the required normal load was applied through lever mechanism. The sliding radius was kept at 80 mm for all tests concerned.

Parameter	Unit	Minimum	Maximum
Wear disc	Mm	100x6	---
Disc speed	RPM	10	800
Pin diameter	Mm	2	10
Pin length	Mm	10	50
Ball diameter	Mm	10	---
Wear track diameter	Mm	10	80
Normal load	N	0	100
Frictional force	N	0	100

**Table 4.1 Specifications of the DUCOM wear and friction monitor**

#### 4.2.2 Wear Parameters:

The variables involved in wear test are:

- % Si in the Al-Si alloy
- Normal load
- Sliding velocity
- Sliding distance
- Lubrication

Wear behavior of the fabricated samples is combined affected by the above parameters. The effect of each individual parameter is studied in these experiments.

#### 4.2.3 Wear measurement:

Wear rate was estimated by measuring the mass loss in the specimen after each test and mass loss,  $\Delta m$  in the specimen was obtained. We can calculate the mass loss by measuring the height loss ( $\Delta h$ ) in each experiment, the area of cross section ( $A$ ) of sample and the density ( $\rho$ ) of the alloy by using the relation

$$\Delta m = \Delta h \times A \times \rho$$

Cares have been taken after each test to avoid interaction of wear debris in the specimen. Wear rate which relates to the mass loss ( $\Delta m$ ) and sliding distance ( $L$ ) was calculated using the expression

$$W = \Delta m / L$$

The friction force was measured for each pass and then averaged over the total number of passes for each wear test. The average value of co-efficient of friction,  $\mu$  of composite was calculated from the expression,

$$\mu = F_f / F_n$$

where  $F_f$  is average friction force and  $F_n$  is applied load.

For characterization of the abrasive wear behavior of the composite, the specific wear rate is employed. This is defined as the volume loss of the composite per unit sliding distance and per unit applied normal load. Often the inverse of specific wear rate expresses in terms of the volumetric wear rate as

$$W_s = W_v / V_s F_n \text{ Where } V_s \text{ is the sliding velocity.}$$

#### 4.2.4 Lubricated wear test:

In this case wear of samples were done in presence of some lubricating medium like engine oil of grade SAE 20W-40. The respective calculations can be done for this condition. The same operating conditions as in dry wear tests were applied except that a continuous flow of the lubricant was supplied to the alloy-abrasive paper interface.





### 4.3 Modeling of Application

CATIA (Computer Aided Three-dimensional Interactive Application) is a multi-platform CAD/CAM/CAE commercial software suite developed by the French company Assault Systems. Written in the C++ programming language, CATIA is the cornerstone of the Assault Systems product lifecycle management software suite.

CATIA offers a solution to shape design, styling, surfacing workflow and visualization to create, modify, and validate complex innovative shapes from industrial design to Class- A surfacing with the ICEM surfacing technologies. CATIA supports multiple stages of product design whether started from scratch or from 2D sketches. CATIA is able to read and produce STEP format files for reverse engineering and surface reuse.

*Fig 4.4 Sketch drawing of model*

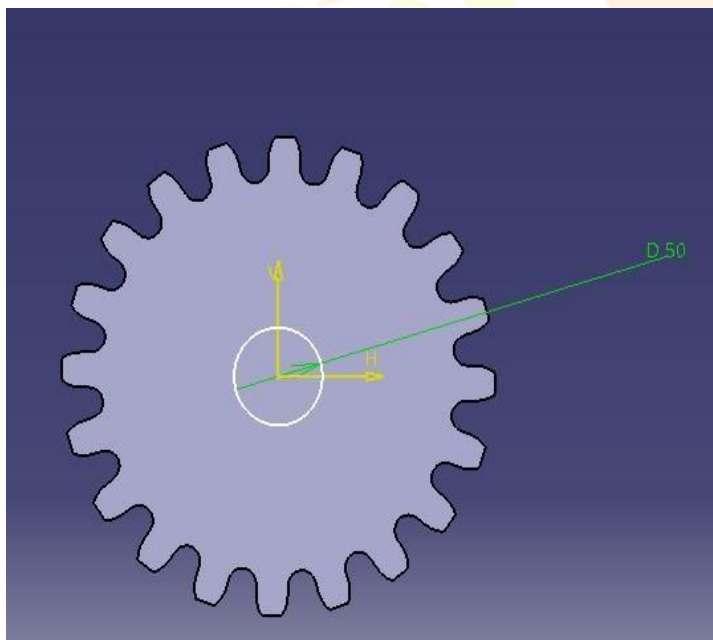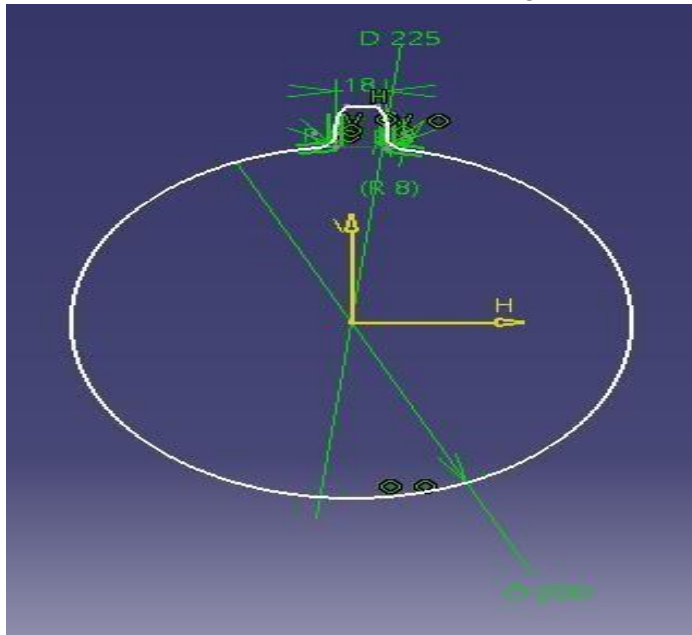

**Fig 4.5 3D Model**

### ***VOLUME FRACTION OF THE SPUR GEAR***

- ALUMINIUM 90% & SILICON 10%
- Aluminum- 450g
- Silicon - 50g, borax powder= 1g

- Weight of the casted blank- 501g
- Amount of aluminum =  $501 \times (90/100)$   
= 450g
- Amount of silicon =  $501 \times (10/100)$   
= 50g
- Weight of gear after machining- 400g
- shrinkage allowances =0.65mm
- machining allowances=1.5mm
- Draft allowances= 0.75mm
- Shake allowances=1mm
- Total allowances=4mm.





**FIG 4.6 PHOTOGRAPHIC VIEW OF THE SPUR GEAR ACKNOWLEDGMENT**

#### **4.RESULT AND DISCUSSION**

##### **5.1 Static structural analysis**

The static structural analysis is done for 15000 N load as the maximum load for gears. The analysis is done as deformation an equivalent stress for all the compositions

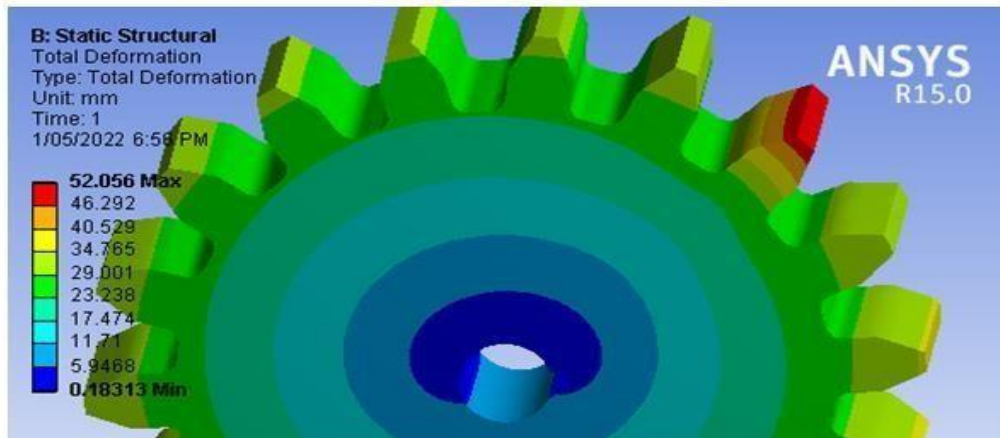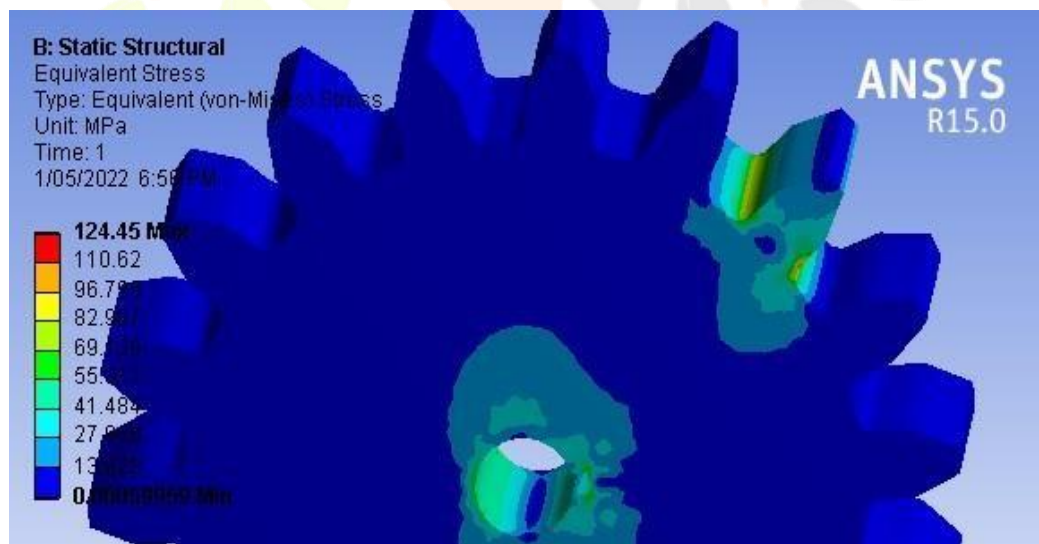

**Fig 5.1 Deformation analysis for the composition 7% OF Si****Fig 5.2 Total equivalent stress fir the composition 7% Si****Fig 5.3 Deformation analysis for the composition 10% OF Si****Fig 5.4 Total equivalent stress fir the composition 10% Si**

From the analysis it is confirmed that material with a composition of 90% aluminum and 10% silicon carbide shows lesser deformation for an applied load 15000N. So, this material is chosen for manufacturing spur gear. The software ZX

S.NO.	COMPOSITION	ANALYTICAL PARAMETER	F=15000N
1	93% Al + 7% SiC	Total deformation	60.251
		Equivalent stress	125.6



2	90% Al + 10% SiC	Total deformation	52.056
		Equivalent stress	124.45

Fig 5.1 Static structural analysis

## 5.2 MICROSTRUCTURES OF THE AS CAST SAMPLES

The micro structures of the as cast samples were seen under an optical microscope with 100x magnification

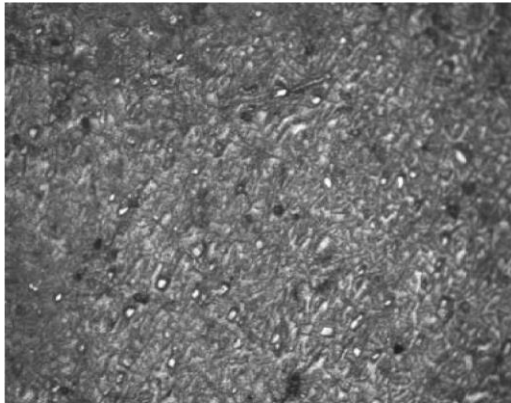


Fig 5.5

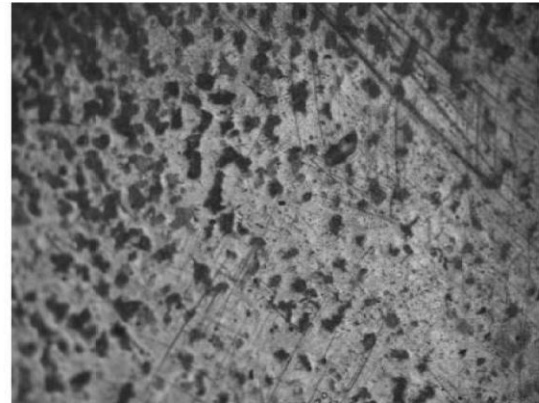


Fig 5.6

**Fig 5.5 Optical microstructures of the as cast alloys Al-7wt%Si Fig 5.6 Optical microstructures of the as cast alloys Al-10wt%Si**

From the above figures it is found that, with increase in silicon percentage in the alloy, the microstructure is different for hypo-eutectic compositions than of the hyper-eutectic composition

## 5.3 HARDNESS:

Alloy composition	Hardness ( $H_v$ )
Al-7wt% Si	55.5
Al-10wt% Si	56.2

**Table 5.2 showing Vicker's Hardness values for as cast alloys**

Hardness is found to increase with increase in Silicon content of the alloy.

## 5.4 RESULTS OF WEAR TESTS:

The wear tests on the samples are carried out (considering the operating parameters of wear) i.e., by varying the sliding velocities, sliding distances, applied load and lubricant conditions. The effects of these parameters have been studied. Relationship between Cumulative Mass Loss (CML) with time, wear rate dependence of sliding distance etc. have been correlated.

### 5.4.1 EFFECT OF NORMAL LOAD

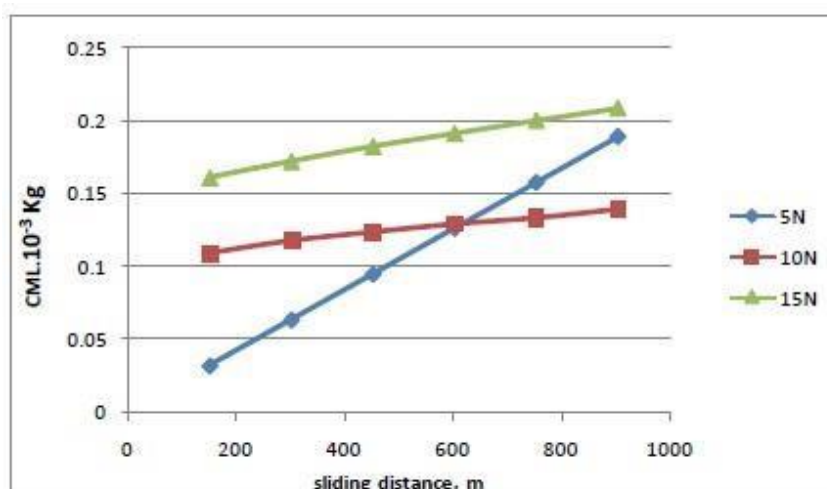


Fig. 5.7 Variation of Cumulative Mass Loss (CML) with sliding distance for Al-10wt% Si at 100rpm sliding speed

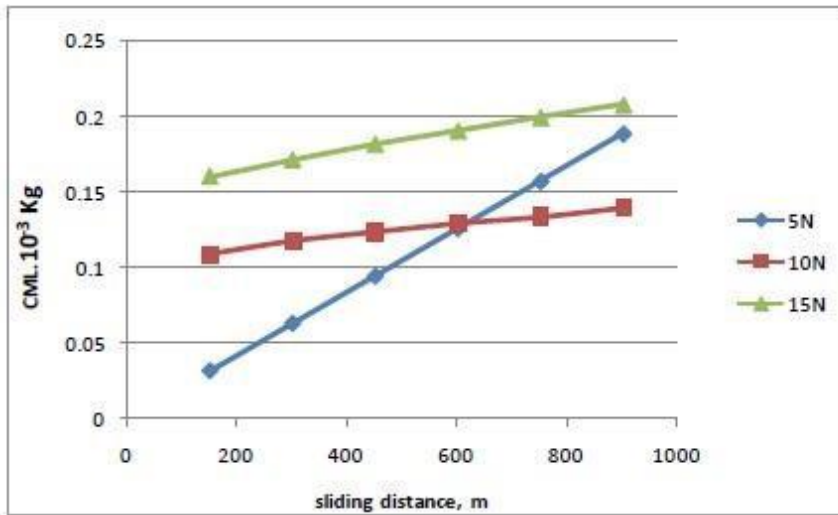


Fig.5.8 Wear rate against sliding distance for Al-10wt%Si at 0.837 m/s sliding speed

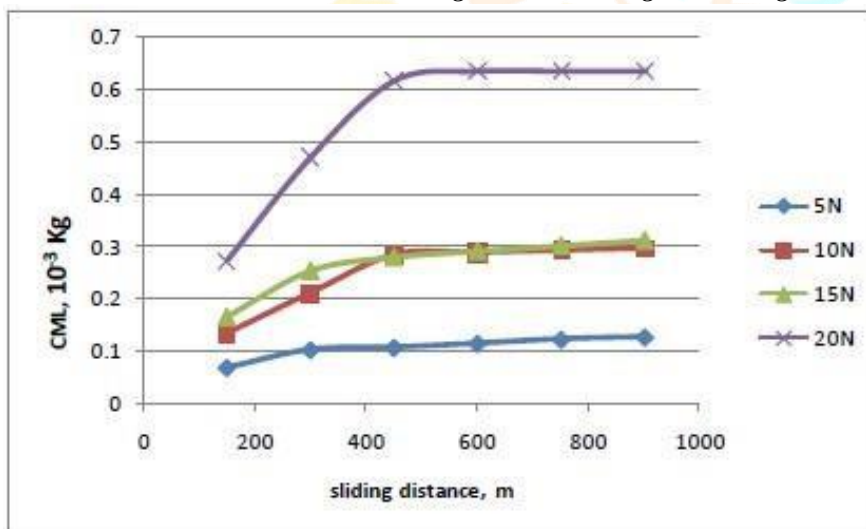


Fig. 5.9 CML against sliding distance for Al-7wt%Si at 0.837 m/s sliding speed

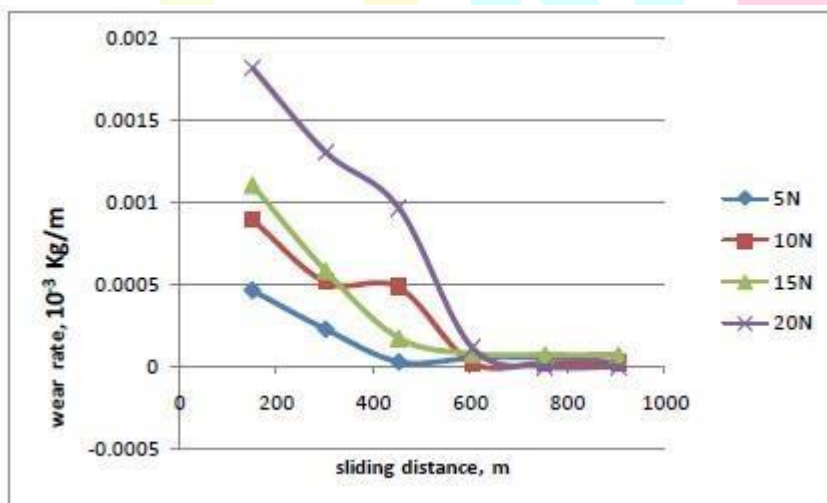


Fig.5.10 Wear rate against sliding distance for Al-7wt%Si at 0.837 m/s sliding speed.

From the above figures, it can be said that, (i) with increase in applied load wear rate increases and (ii) after a sliding distance of about 400 mts. Rate of wear attains a steady state.

The effect of environmental conditions (i.e., dry and lubricated) on wear behavior is represented in the figures 5.11 to 5.16. It can be said that, the mass loss of the material is higher in case of the samples abraded with SAE 20W-40 grade engine oil than that of the dry abrasive test condition. It may be due to the fact that, the lubricants have filled the micro voids of the fiber dusts which have filled (the void spaces) with lubricant and hence caused the enhanced wear rate. However, this attains a steady state after a sliding distance of 1000 meters beyond.

#### 4.5 SCANNING ELECTRON MICROSCOPY

The scanning electron micrographs for the worn surfaces in both unlubricated and lubricated conditions are obtained at magnifications of 1500x and 500x. The micrographs of the samples at unlubricated conditions are shown in fig.5.11, 5.12, respectively for Al-7%, Al-10% Si alloys. And rest figures are for lubricated conditions, for the same sequences of the compositions.

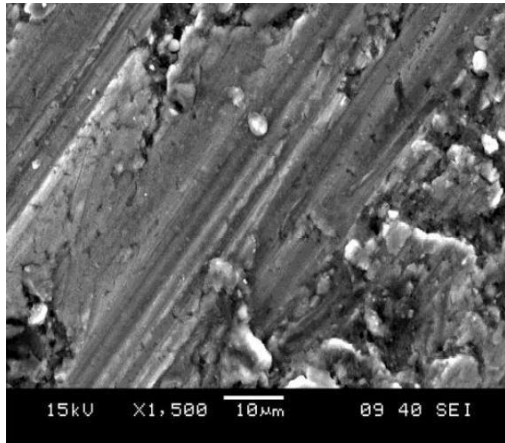


Fig5.12

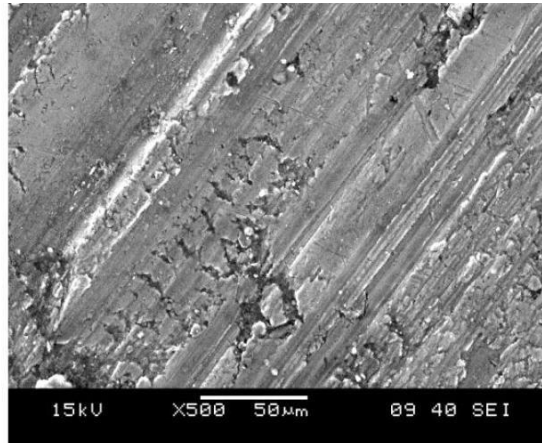


Fig5.11

The micrographs of Al-7wt% Si samples tested in lubricated condition are shown below.

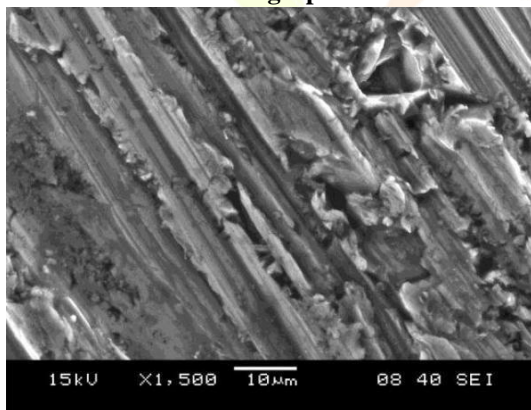


Fig 5.13

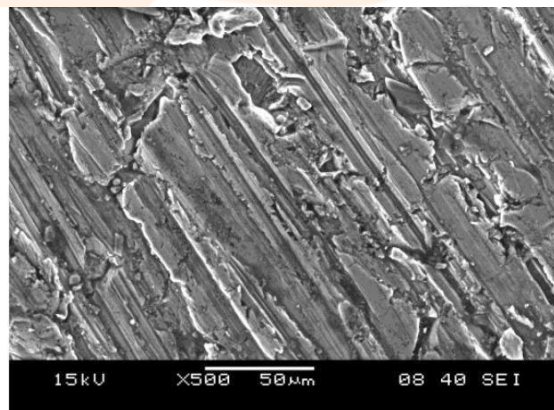


Fig 5.14

The micrographs of Al-10wt% Si samples tested in unlubricated condition are shown below.

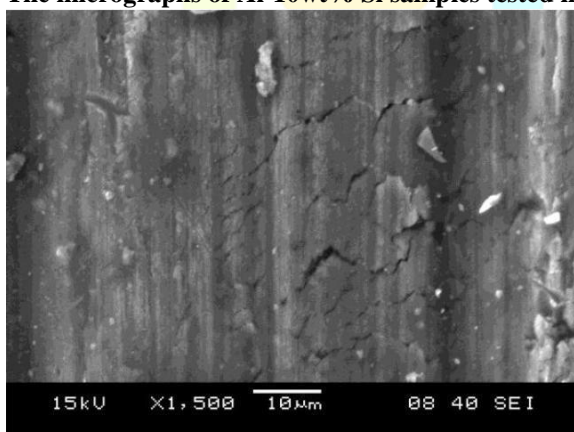


Fig 5.15


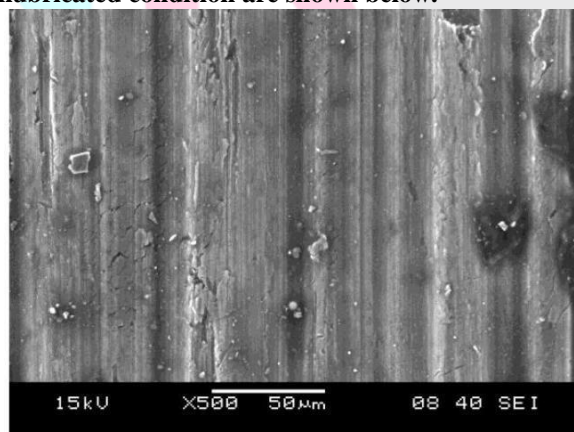


Fig 5.16

The micrographs of Al-10wt% Si samples tested in lubricated condition are shown below

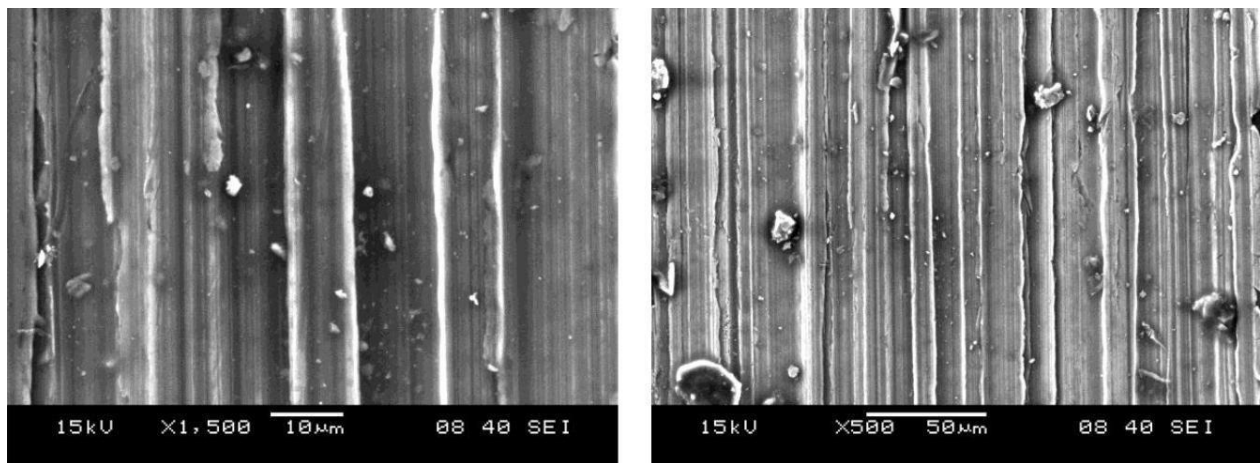

**Fig 5.17****Fig 5.18**

The worn surface after dry sliding of Al-7wt% (fig 5.11 and 5.12) shows deep well separated grooves. Cracks are also observed which are spread perpendicular to the sliding direction. Comparing it with the SEM of worn surface at lubricated condition (fig 5.13 and 5.14), It is found that the grooves are along the sliding direction, but not many cracks are seen. However, crack propagation is seen along the same direction as sliding.

With increase in silicon content in the alloys that is 10% and 14% silicon, reveals different micrographs. For Al-10wt% Si, the worn surface shown (fig 5.15, 5.16 and fig 5.17 and 5.18) for the sample tested in dry and lubricated conditions respectively. It can be observed that although deeper grooves/abrasive tracks are observed but are smooth in dry condition and at lubricated condition the separation of groove line is reduced. This may be due to the fact that at dry condition the wear debris (of the material) might have flown off, but in lubricated condition some particles are embedded in the matrix which is the reason for deeper groove.

## 6.CONCLUSION

In this work aluminum silicon metal matrix composite material is suggested for the manufacture of spur gears. The MMC is prepared and tested by both mechanically and numerically. The results show that this MMC has properties that can replace the material that is used conventionally. Better results have been obtained when the composition is of 90% aluminum and 10% silicon. Gears manufactured from this material provides 60% less weight compared to the conventional gears. Thus, providing more life than conventional gears. These gears can be able to transmit 40kW power. These gears can be used in automobiles where spur gears find an application

From this piece of experimentations following conclusions can be drawn.

- Wear behavior is dependent on applied load, sliding speed mainly. However, a steady state is attained after a sliding distance of about 1000 meters in all cases.
- Wear is seen to increase at higher sliding speed and at higher applied load.
- With increase in silicon percent, the CML and wear rate decreases.
- In case of lubricated condition, the specimen's shows higher amount of material loss i.e., higher wear rate, which is not clear at the moment. But is expected that, the precipitated silicon platelets have been easily removed from the material due to interaction at the inter boundary zone of Al-Si eutectic and silicon platelets (i.e., pro-eutectic silicon) and has enhanced the material loss.
- ANSYS Results of Si 10% is better results.

## 7.REFERENCE

1. Elwin L. Rooy "Introduction to Aluminium and Aluminum Alloys" ASM Handbook Vol-02, Page567
2. Srivastava V.C, Mandal R.K, Ojha S.N, "Evolution of microstructure in spray formed Al-18%Si alloy", Materials Science and Engineering, Vol- A 383 (2004), pages-14-20
3. Singh Vijendra, "Physical Metallurgy", Delhi, Standard Publishers Distributors, 2008, pages-679680
4. Hatch John E, "Aluminum: Properties and Physical Metallurgy", ASM,
  - a. 1984, Metals Park, Ohio, page -998
5. Williams John Austin, "Engineering Tribology", New York,
  - a. Cambridge University Press, 2005, page-165
6. Phakatkar H.G, Ghorpade R.R, "Tribology", Nirali Prakashan, Pune, 2009
7. Tylczak Joseph H., Oregon Albany, "Abrasive Wear", Wear, ASM handbook, vol-18, page-345 - 563
8. Kosel Thomas H, "Solid Particle Erosion", Wear, ASM handbook, vol-18
9. Ludema K C, "Sliding and Adhesive wear", Wear, ASM handbook, vol
  - a. Waterhouse R.B, "fretting wear", wear, ASM handbook vol-2, page-456

10. Kato K, "Classification of wear mechanisms/models", Wear-materials, mechanisms and practice, John Wiley & Sons, New York, Madse Brent W, "Corrosive Wear", Wear, ASM handbook, vol-18, Page-789.
11. Engel Peter, "Impact Wear", wear, ASM handbook, vol-18, Page- 678
12. G. Rajaram, S. Kumaran and T. Srinivas Rao., "Studies on High Temperature and Mechanism of AlSi/Graphite Composite Under Dry Sliding Conditions (2017) 13. Madse, Brent W., "Corrosive Wear", Wear, ASM handbook, Vol. 18.
14. Engel, P., "Impact Wear", wear, ASM handbook, Vol. 18.
15. Yasmin, T., Khalid, Asad A., Haque M.M, "Tribological (wear) properties of aluminum–silicon eutectic base alloy under dry sliding condition",
16. Journal of Materials Processing Technology, Vol. 153–154, 2004, pp. 833838.
17. Kori, S.A., Chandrasekhara T M, "Studies on the dry sliding wear behavior of hypoeutectic and eutectic Al–Si alloys", Wear, Vol. 263, 2007, pp. 745-755.
18. Rajaram, G., Rao, T.S., "High temperature tensile and wear behavior of aluminum silicon alloy", Materials Science and Engineering A, Vol. 528, 2010, pp. 247- 253.
19. Dwivedi, D.K., "Wear behaviour of cast hypereutectic Aluminum silicon alloys", Materials and Design, Vol. 27, 2006, pp. 610–616.
20. Turabian, H., Pathak J.P., Tiwari S.N., "Wear characteristics of Al-Si alloys", Wear, Vol. 172, 1994, pp. 49-58.
21. Anasyida, A. S., Daud, A. R., Ghazali, M. J., "Dry sliding wear behaviour of al-4si-4mg alloys by addition of cerium", International Journal of Mechanical and Materials Engineering, Vol. 4, 2009, pp. 127-130

